


# GGB DU<sup>®</sup> and DU-B

Metal-Polymer Self-lubricating Bearing Solutions



The Global Leader  
in High Performance Bearing Solutions

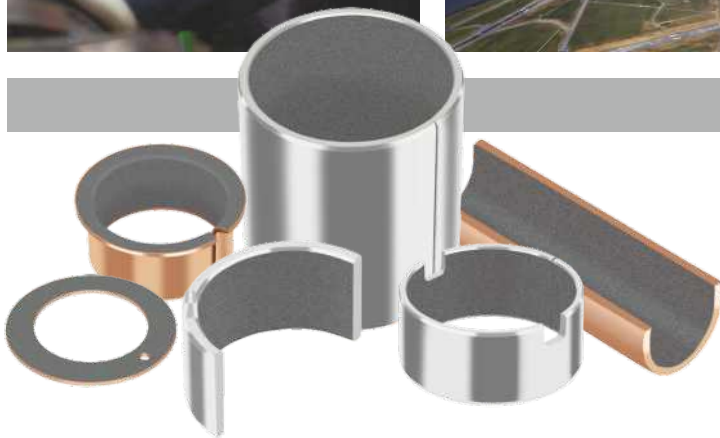

an EnPro Industries company

## Quality

All the products described in this handbook are manufactured under DIN EN ISO 9001, ISO/TS 16949 and ISO 14001 approved quality management systems.

In addition GGB North America has been certified AS9100 revision B complying with the requirements of aerospace industry's quality management system for the manufacture of metal-backed bearings and filament wound bearings and washers.

### AMERICA



### FRANCE



### CHINA



### GERMANY



### BRAZIL



### SLOVAKIA



### Technical approvals:

Tested and approved by MPA Stuttgart (for DU<sup>®</sup>B) for structural bearings for civil engineering applications.

## Content

<b>1 Introduction</b> .....	<b>5</b>	<b>4 Data Sheet</b> .....	<b>22</b>
1.1 Applications .....	5	4.1 Data for bearing design calculations .....	22
1.2 Characteristics and Advantages .....	5	<b>5 Lubrication</b> .....	<b>23</b>
1.3 Basic Forms Available .....	5	5.1 Lubricants .....	23
1.4 Materials .....	6	5.2 Tribology .....	23
<b>2 Material</b> .....	<b>7</b>	Hydrodynamic lubrication .....	23
2.1 Structure .....	7	Mixed film lubrication .....	24
2.2 Dry Wear Mechanism .....	7	Boundary lubrication .....	24
2.3 Physical, Mechanical and Electrical Properties .....	9	5.3 Characteristics of Lubricated DU bearings .....	24
2.4 Chemical Properties .....	10	5.4 Design Guidance for Lubricated Applications .....	24
Electrochemical Corrosion .....	10	5.5 Clearances for lubricated operation .....	26
2.5 Frictional Properties .....	10	5.6 Mating Surface Finish for lubricated operation .....	26
<b>3 Performance</b> .....	<b>12</b>	5.7 Grooving for lubricated operation .....	26
3.1 Design Factors .....	12	5.8 Grease Lubrication .....	26
Calculation .....	12	<b>6 Bearing Assembly</b> .....	<b>27</b>
3.2 Specific Load $\bar{p}$ .....	12	Dimensions and Tolerances .....	27
3.3 Specific Load Limit $\bar{p}_{lim}$ .....	13	6.1 Allowance for Thermal Expansion .....	27
3.4 Sliding Speed $U$ .....	13	6.2 Tolerances for minimum clearance .....	27
Continuous Rotation .....	13	Sizing .....	28
Oscillating Movement .....	13	6.3 Counterface Design .....	28
3.5 $\bar{p}U$ Factor .....	14	6.4 Installation .....	29
3.6 Application Factors .....	14	Fitting of cylindrical bushes .....	29
Temperature .....	14	Fitting of flanged bushes .....	29
Mating Surface .....	15	Insertion Forces .....	29
Bearing Size .....	15	Alignment .....	30
Bore Burnishing .....	16	Sealing .....	30
Type of Load .....	16	6.5 Axial Location .....	30
3.7 Calculation of Bearing Size ..	17	Fitting of Thrust Washers .....	30
Calculation for Bushes .....	17	Slideways .....	31
Calculation for Thrust Washers ..	17	<b>7 Modification</b> .....	<b>32</b>
Calculation for Slideways .....	17	7.1 Cutting and Machining .....	32
3.8 Calculation of Bearing Service Life .....	18	Drilling Oil Holes .....	32
Specific load $\bar{p}$ .....	18	Cutting Strip Material .....	32
High load factor $a_E$ .....	18	7.2 Electroplating .....	32
Modified $\bar{p}U$ Factor .....	18	DU Components .....	32
Estimation of bearing life $L_H$ .....	19	Mating Surfaces .....	32
Bore Burnishing .....	19		
Slideways .....	19		
3.9 Worked Examples .....	20		

---

<b>8</b>	<b>Standard Products</b>	<b>33</b>	<b>9</b>	<b>Test Methods</b>	<b>51</b>
8.1	DU Cylindrical Bushes	33	9.1	Measurement of	
8.2	DU Flanged Bushes	38		<b>Wrapped Bushes</b>	<b>51</b>
8.3	DU Flanged Washers	40		Test A of ISO 3547 Part 2	51
8.4	DU Thrust Washer	41		Test B (alternatively to Test A)	51
8.5	DU-B Cylindrical Bushes	42		Test C	51
8.6	DU-B Flanged Bushes	44		Measurement of Wall Thickness	
8.7	DU Cylindrical Bushes -			(alternatively to Test C)	51
	Inch sizes	45		Test D	51
8.8	DU Thrust Washers -			<b>Formula Symbols and</b>	
	Inch sizes	49		<b>Designations</b>	<b>53</b>
8.9	DU Strip	50		<b>Product Information</b>	<b>55</b>
8.10	DU-B Strip	50			
8.11	DU Strip - Inch sizes	50			



# 1 Introduction

The purpose of this handbook is to provide comprehensive technical information on the characteristics of DU<sup>®</sup> bearings.

The information given permits designers to establish the correct size of bearing required and the expected life and performance.

GGB Research and Development services are available to assist with unusual design problems.

Complete information on the range of DU standard stock products is given together with details of other DU products.

GGB is continually refining and extending its experimental and theoretical knowledge and, therefore, when using this brochure it is always worth-while to contact the Company should additional information be required.

As it is impossible to cover all conditions of operation which arise in practice, customers are advised to carry out prototype testing wherever possible.

## 1.1 Applications

DU is suitable for

- rotating,
- oscillating,
- reciprocating and
- sliding movements.

Also available are DU related material compositions for specific applications, for

example when increased corrosion resistance of the bearing material is required due to

- atmospheric or environmental considerations
- food safety regulations

## 1.2 Characteristics and Advantages

- **DU requires no lubrication**
- **Provides maintenance free operation**
- **DU has a high  $\bar{\rho}$ U capability**
- **DU exhibits low wear rate**
- **Seizure resistant**
- **Suitable for temperatures from -200 to +280 °C**
- **High static and dynamic load capacity**
- **Good frictional properties with negligible stick-slip**
- **Resists solvents**
- **No water absorption and therefore dimensionally stable**
- **DU is electrically conductive and shows no electrostatic effects**
- **DU has good embedability and is tolerant of dusty environments**
- **Compact and light**
- **DU bearings are prefinished and require no machining after assembly**

## 1.3 Basic Forms Available

**Standard Components available from stock.**

These products are manufactured to International, National or GGB standard designs.

### **Metric and Imperial sizes**

- Cylindrical Bushes
- Flanged Bushes \*
- Thrust Washers
- Flanged Washers \*
- Strip Material

\* Metric sizes only



Fig. 1: Standard Components

**Non-Standard Components not available from stock.**

- These products are manufactured to customers' requirements with or without GGB recommendations, and include for example
- Half Bearings
  - Flat Components
  - Deep Drawn Parts
  - Pressings
  - Stampings
- Modified Standard Components

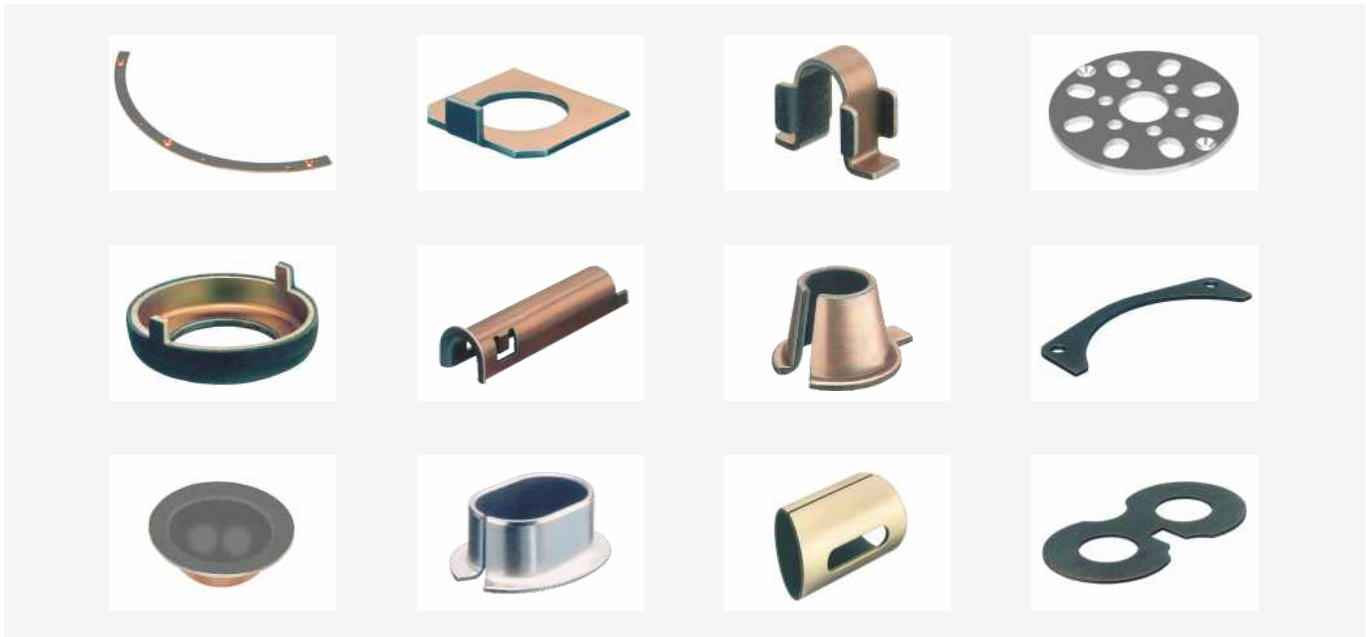


Fig. 2: Non-Standard Components

## 1.4 Materials

Material	Backing	Bearing Lining	Operating Temperature [°C]		Maximum Load $\bar{p}_{lim}$ [N/mm <sup>2</sup> ]
			Minimum	Maximum	
DU	Steel	PTFE+Lead	-200	+280	250
DUB	Bronze	PTFE+Lead	-200	+280	140

Table 1: Characteristics of DU and DU-B

## 2 Material

### 2.1 Structure

#### DU

DU and DU-B take advantage of the outstanding dry bearing properties of Polytetrafluoroethylene (PTFE) and combines them with strength, stability and good wear resistance, excellent heat conductivity and low thermal expansion.

DU consists of three bonded layers: a steel backing strip and a porous bronze matrix, impregnated and overlaid with the PTFE/lead bearing material.



Fig. 3: DU Microsection

#### DU-B

DU-B also consists of three layers, with a bronze backing replacing the steel backing strip. The structure is otherwise the same as that of DU.

The bronze backing provides a high corrosion resistance, anti magnetic properties and a good thermal conductivity.



Fig. 4: DU-B Microsection

### 2.2 Dry Wear Mechanism

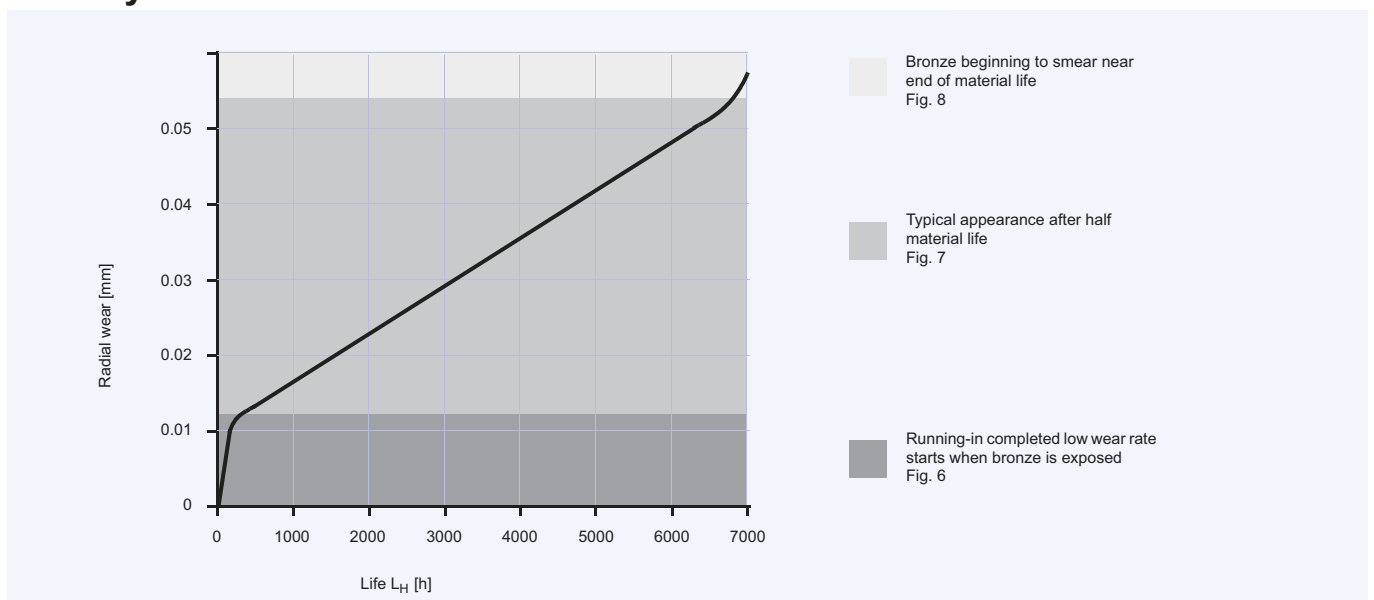


Fig. 5: Effect of wear on the DU bearing surface under dry operating conditions.

### Running-in

During normal operation, a DU bearing quickly beds in and the PTFE/lead overlay material removed during this period, typically 0.015 mm, is transferred to the mating surface and forms a physically bonded lubricant film.

The rubbing surface of the bearing often acquires a grey-green colour and the bronze matrix can be seen exposed over about 10 % of the bearing surface. Any

excess of the PTFE/lead surface layer will be shed as fine feathery particles.

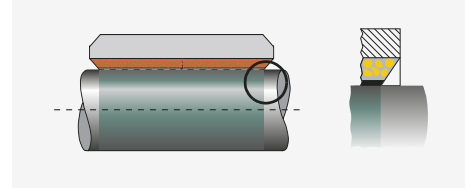


Fig. 6: Running-in

### After 50 % of useful life

Following the running-in period the wear rate reduces to a minimum and the percentage of bronze exposed gradually increases.

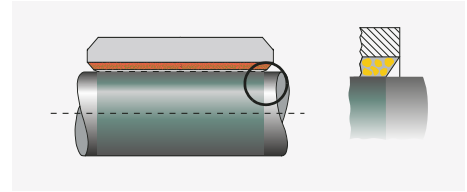


Fig. 7: After 50 % of useful life

### End of useful life

After an extended period of operation the wear rate increases as the component approaches the end of its useful life as a self-lubricating bearing. At this stage at least 70 % of the bearing surface will be exposed bronze, and approximately 0.06 mm wear will have occurred.

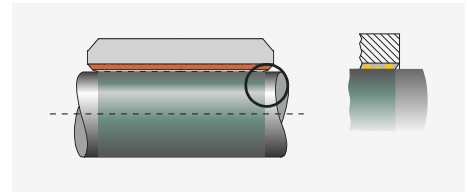


Fig. 8: End of useful life

### Wear of Mating Surfaces

There is no measurable wear of mating surfaces made from recommended materials unless a DU bearing is operated

beyond its useful life or becomes contaminated with abrasive dirt.



## 2.3 Physical, Mechanical and Electrical Properties

Characteristic	Symbol	Value		Unit	Comments	
		DU	DU-B			
Physical Properties	Thermal Conductivity	$\lambda$	40	60	W/mK	after running in.
	Coefficient of linear thermal expansion :					measured on strip 1.9 mm thick.
	parallel to surface	$\alpha_1$	11	18	1/10 <sup>6</sup> K	
	normal to surface	$\alpha_2$	30	36	1/10 <sup>6</sup> K	
	Maximum Operating Temperature	$T_{max}$	+280	+280	°C	
Minimum Operating Temperature	$T_{min}$	-200	-200	°C		
Mechanical Properties	Compressive Yield Strength	$\sigma_c$	350	300	N/mm <sup>2</sup>	measured on disc 25 mm diameter x 2.44 mm thick.
	Maximum Load					
	Static	$\bar{p}_{sta,max}$	250	140	N/mm <sup>2</sup>	
	Dynamic	$\bar{p}_{dyn,max}$	140	140	N/mm <sup>2</sup>	
Electrical Properties	Surface Resistance	$R_{OB}$	1 – 10	1 – 12	$\Omega$	depends on applied pressure and contact area
Nuclear Radiation Resistance	Maximum Thermal Neutron dose	$D_{Nth}$	$2 \times 10^{15}$	$2 \times 10^{15}$	nvt	nvt = thermal neutron flux
	Maximum gamma ray dose	$D_\gamma$	$10^6$	$10^6$	Gy = J/kg	1 Gray = 1 J/kg

Table 2: Properties of DU and DU-B

## 2.4 Chemical Properties

The following table provides an indication of the chemical resistance of DU and DU-B to various chemical media. It is recommen-

ded that the chemical resistance is confirmed by testing if possible.

	Chemical	%	°C	DU	DU-B
Strong Acids	Hydrochloric Acid	5	20	-	-
	Nitric Acid	5	20	-	-
	Sulphuric Acid	5	20	-	-
Weak Acids	Acetic Acid	5	20	-	o
	Formic Acid	5	20	-	o
Bases	Ammonia	10	20	o	-
	Sodium Hydroxide	5	20	o	o
Solvents	Acetone		20	+	+
	Carbon Tetrachloride		20	+	+
Lubricants and Fuels	Paraffin		20	+	+
	Gasolene		20	+	+
	Kerosene		20	+	+
	Diesel Fuel		20	+	+
	Mineral Oil		70	o	o
	HFA-ISO46 High Water Fluid		70	o	o
	HFC-Water-Glycol		70	-	-
	HFD-Phosphate Ester		70	o	o
	Water		20	o	+
	Sea Water		20	-	o

Table 3: Chemical Resistance of DU and DU-B

+	<p><b>Satisfactory:</b> Corrosion damage is unlikely to occur.</p>
o	<p><b>Acceptable:</b> Some corrosion damage may occur but this will not be sufficient to impair either the structural integrity or the tribological performance of the material.</p>
-	<p><b>Unsatisfactory:</b> Corrosion damage will occur and is likely to affect either the structural integrity and/or the tribological performance of the material.</p>

### Electrochemical Corrosion

DU-B should not be used in conjunction with aluminium housings due to the risk of

electrochemical corrosion in the presence of water or moisture.

## 2.5 Frictional Properties

DU bearings show negligible 'stick-slip' and provide smooth sliding between adjacent surfaces. The coefficient of friction of DU depends upon:

- The specific load  $\bar{p}$  [N/mm<sup>2</sup>]
- The sliding speed U [m/s]
- The roughness of the mating running surface  $R_a$  [ $\mu$ m]

- The bearing temperature T [°C].

A typical relationship is shown in Fig. 9, which can be used as a guide to establish the actual friction under clean, dry conditions after running in.

Exact values may vary by  $\pm 20\%$  depending on operating conditions.

Before running in, the friction may be up to 50 % higher.

With frequent starts and stops, the static coefficient of friction is approximately equal to, or even slightly less than the dynamic coefficient of friction.

After progressively longer periods of dwell under load (e.g. hours or days) the static

coefficient of friction on the first movement may be between 1.5 and 3 times greater, particularly before running in.

Friction increases at bearing temperatures below 0 °C.

Where frictional characteristics are critical to a design they should be established by prototype testing.

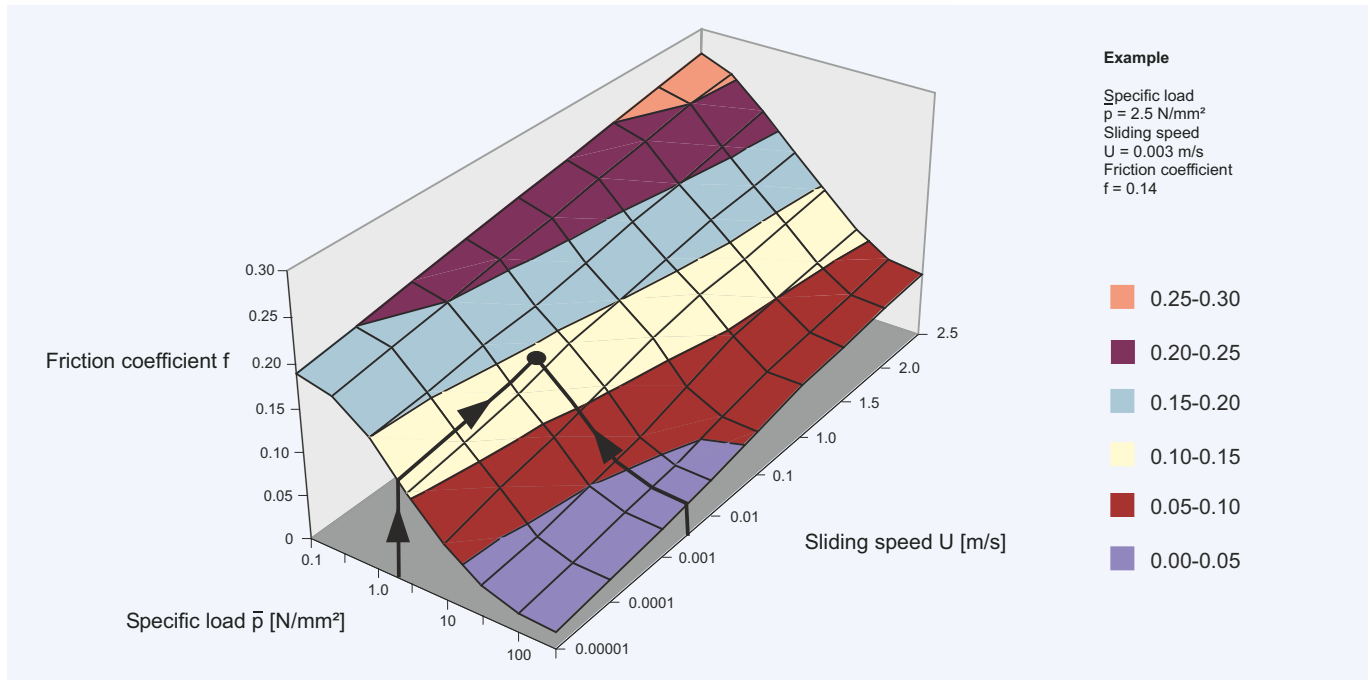


Fig. 9: Variation of friction coefficient  $f$  with specific load  $\bar{p}$  and sliding speed  $U$  at temperature  $T = 25 \text{ °C}$

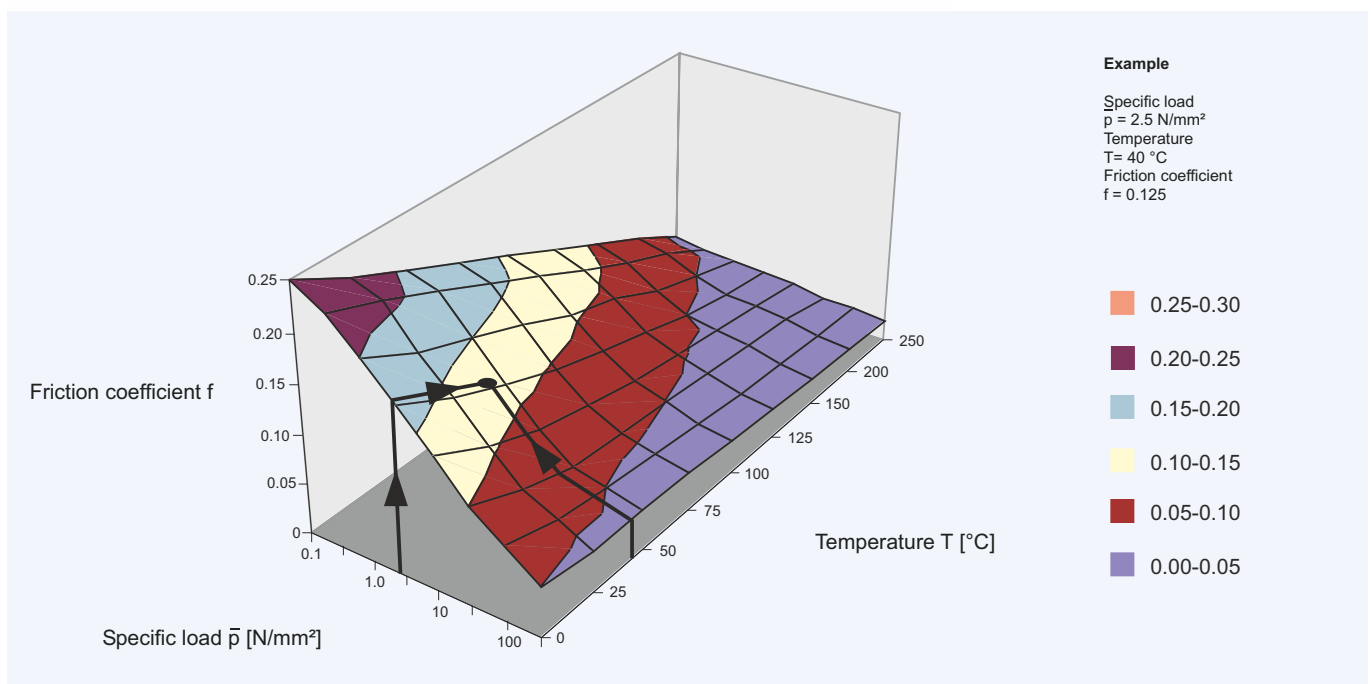


Fig. 10: Variation of friction coefficient  $f$  with specific load  $\bar{p}$  and temperature  $T$  at sliding speed  $U = 0.01 \text{ m/s}$

## 3 Performance

### 3.1 Design Factors

The main parameters when determining the size or calculating the service life for a DU bearing are:

- Specific Load Limit  $\bar{p}_{lim}$
- $\bar{p}U$  Factor

- Mating surface roughness  $R_a$
- Mating surface material
- Temperature  $T$
- Other environmental factors e.g. housing design, dirt, lubrication

#### Calculation

Two design procedures are provided as follows:

- A bearing service life calculation based on the permitted bearing dimensions

- A calculation of the necessary bearing dimensions based on the required bearing service life

### 3.2 Specific Load $\bar{p}$

For the purpose of assessing bearing performance the specific load  $\bar{p}$  is defined as the working load divided by the projected

area of the bearing and is expressed in  $N/mm^2$ .

#### Cylindrical Bush

(3.2.1) [N/mm<sup>2</sup>]

$$\bar{p} = \frac{F}{D_i \cdot B}$$

#### Flanged Bush (Axial Loading)

(3.2.3) [N/mm<sup>2</sup>]

$$\bar{p} = \frac{F}{0.04 \cdot (D_o^2 - D_i^2)}$$

#### Thrust Washer

(3.2.2) [N/mm<sup>2</sup>]

$$\bar{p} = \frac{4F}{\pi \cdot (D_o^2 - D_i^2)}$$

#### Slideway

(3.2.4) [N/mm<sup>2</sup>]

$$\bar{p} = \frac{F}{L \cdot W}$$

Permanent deformation of the DU bearing lining may occur at specific loads above  $140 N/mm^2$  and under these conditions DU should only be used with slow intermittent movements.

The permissible maximum load on a thrust washer is higher than that on the flange of a flanged bush, and under conditions of high axial loads a thrust washer should be specified.

### 3.3 Specific Load Limit $\bar{p}_{lim}$

The maximum load which can be applied to a DU bearing can be expressed in terms of the Specific Load Limit, which depends on the type of the loading. It is highest under steady loads. Conditions of dynamic load or oscillating movement which produce fatigue stress in the bearing result in a reduction in the permissible Specific Load Limit.

In general the specific load on a DU bearing should not exceed the Specific Load Limits given in Table 4.

The values of Specific Load Limit specified in Table 4 assume good alignment between the bearing and mating surface (Fig. 29).

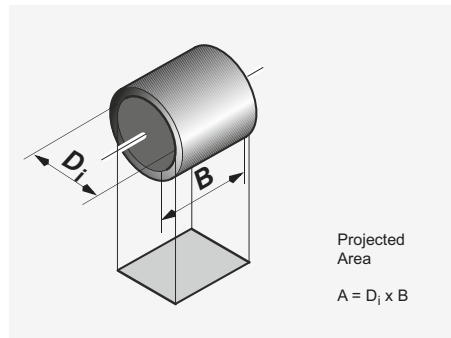


Fig. 11: Projected Area

#### Maximum specific load $\bar{p}_{lim}$

Type of loading	$\bar{p}_{lim}$ [N/mm <sup>2</sup> ]										
steady load, rotating movement	140										
steady load, oscillating movement											
$\bar{p}_{lim}$	140	140	115	95	85	80	60	44	30	20	
No. of movement cycles Q	1000	2000	4000	6000	8000	10 <sup>4</sup>	10 <sup>5</sup>	10 <sup>6</sup>	10 <sup>7</sup>	10 <sup>8</sup>	
dynamic load, rotating or oscillating movement											
$\bar{p}_{lim}$	60	60	50	46	42	40	30	22	15	10	
No. of load cycles Q	1000	2000	4000	6000	8000	10 <sup>4</sup>	10 <sup>5</sup>	10 <sup>6</sup>	10 <sup>7</sup>	10 <sup>8</sup>	

Table 4: Maximum specific load  $\bar{p}_{lim}$

### 3.4 Sliding Speed U

Speeds in excess of 2.5 m/s sometimes lead to overheating, and a running in procedure may be beneficial.

This could consist of a series of short runs progressively increasing in duration from an initial run of a few seconds.

#### Calculation of Sliding Speed U [m/s]

##### Continuous Rotation

###### Cylindrical Bush

$$(3.4.1) \quad U = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3} \quad [\text{m/s}]$$

###### Thrust Washer

$$(3.4.2) \quad U = \frac{D_o + D_i}{2} \cdot \pi \cdot N \cdot \frac{1}{60 \cdot 10^3} \quad [\text{m/s}]$$

##### Oscillating Movement

###### Cylindrical Bush

$$(3.4.3) \quad U = \frac{D_i \cdot \pi}{60 \cdot 10^3} \cdot \frac{4\phi \cdot N_{osz}}{360} \quad [\text{m/s}]$$

###### Thrust Washer

$$(3.4.4) \quad U = \frac{D_o + D_i}{2} \cdot \pi \cdot \frac{4\phi \cdot N_{osz}}{60 \cdot 10^3 \cdot 360} \quad [\text{m/s}]$$

## 3.5 $\bar{p}U$ Factor

The useful operating life of a DU bearing is governed by the  $\bar{p}U$  factor, the product of the specific load  $\bar{p}$  [N/mm<sup>2</sup>] and the sliding speed  $U$  [m/s].

For thrust washers and flanged bush thrust faces the rubbing velocity at the mean diameter is used.

$\bar{p}U$  factors up to 3.6 N/mm<sup>2</sup> x m/s can be accommodated for short periods, whilst for continuous rating.

$\bar{p}U$  factors up to 1.8 N/mm<sup>2</sup> x m/s can be used, depending upon the operating life required.

	DU	Unit
$\bar{p}$	140	N/mm <sup>2</sup>
$U$	2.5	m/s
$\bar{p}U$ continuous	1.8	N/mm <sup>2</sup> x m/s
$\bar{p}U$ intermittent	3.6	N/mm <sup>2</sup> x m/s

Table 5: Typical data  $\bar{p}$ ,  $U$  and  $\bar{p}U$

### Calculation of $\bar{p}U$ Factor [N/mm<sup>2</sup> x m/s]

$$(3.5.1) \quad \bar{p}U = \bar{p} \cdot U \quad [\text{N/mm}^2 \times \text{m/s}]$$

## 3.6 Application Factors

The following factors influence the bearing performance of DU and must be considered in calculating the required dimension

or estimating the bearing life for a particular application.

### Temperature

The useful life of a DU bearing depends upon the operating temperature.

Under dry running conditions frictional heat is generated at the rubbing surface of the bearing dependent on the  $\bar{p}U$  condition. For a given  $\bar{p}U$  factor the operating temperature of the bearing depends upon the temperature of the surrounding environ-

ment and the heat dissipation properties of the housing. Intermittent operation affects the heat dissipation from the assembly and hence the operating temperature of the bearing.

The effect of temperature on the operating life of DU bearings is indicated by the factor  $a_T$  shown in Table 6.

Mode of Operation	Nature of housing	Temperature of bearing environment $T_{amb}$ [°C] and Temperature application factor $a_T$					
		25	60	100	150	200	280
Dry continuous operation	Average heat dissipating qualities	1.0	0.8	0.6	0.4	0.2	0.1
Dry continuous operation	Light pressings or isolated housing with poor heat dissipating qualities	0.5	0.4	0.3	0.2	0.1	-
Dry continuous operation	Non-metallic housings with bad heat dissipating qualities	0.3	0.3	0.2	0.1	-	-
Dry intermittent operation (duration less than 2 min, followed by a longer dwell period)	Average heat dissipating qualities	2.0	1.6	1.2	0.8	0.4	0.2
Continuously immersed in water		2.0	1.5	0.6	-	-	-
Alternately immersed in water & dry		0.2	0.1	-	-	-	-
Continuously immersed in non lubricant liquids other than water		1.5	1.2	0.9	0.6	0.3	0.1
Continuously immersed in lubricant		3.0	2.5	2.0	1.5	-	-

Table 6: Temperature application factor  $a_T$



## Mating Surface

The effect of the mating surface material type on the operating life of DU bearings is indicated by the mating surface factor  $a_M$  and the life correction constant  $a_L$  shown in Table 7.

Material	$a_M$	$a_L$
<b>Steel and Cast Iron</b>		
Carbon Steel	1	200
Carbon Manganese Steel	1	200
Alloy Steel	1	200
Case Hardened Steel	1	200
Nitrided Steel	1	200
Salt bath nitrocarburised	1	200
Stainless Steel (7-10 % Ni, 17-20 % Cr)	2	200
Sprayed Stainless Steel	1	200
Cast Iron(0.3 $\mu\text{m}$ $R_a$ )	1	200

Material	$a_M$	$a_L$
<b>Plated Steel with minimum thickness of plating 0.013 mm</b>		
Cadmium	0.2	600
Hard Chrome	2.0	600
Lead	1.5	600
Nickel	0.2	600
Phosphated	0.2	300
Tin Nickel	1.2	600
Titanium Nitride	1.0	600
Tungsten Carbide Flame Plated	3.0	600
Zinc	0.2	600
<b>Non ferrous metals</b>		
Aluminium Alloys	0.4	200
Bronze and Copper Base Alloys	0.1-0.4	200
Hard Anodised Aluminium (0.025 mm thick)	3.0	600

Table 7: Mating surface factor  $a_M$  and life correction constant  $a_L$

### Note:

The factor values given assume a mating surface finish of  $\leq 0.4 \mu\text{m} R_a$

- A ground surface is preferred to fine turned
- Surfaces should be cleaned of abrasive particles after polishing

- Cast iron surfaces should be ground to  $< 0.3 \mu\text{m} R_a$
- The grinding cut should be in the same direction as the bearing motion relative to the shaft

## Bearing Size

The running clearance of a DU bearing increases with bearing diameter resulting in a proportionally smaller contact area between the shaft and bearing. This reduction in contact area has the effect of increasing the actual unit load and hence  $\bar{p}_U$

factor. The bearing size factor (Fig. 13) is used in the design calculations to allow for this effect. The bearing size factor is also applicable to thrust washers, where for other reasons, bearing diameter has an effect on performance.

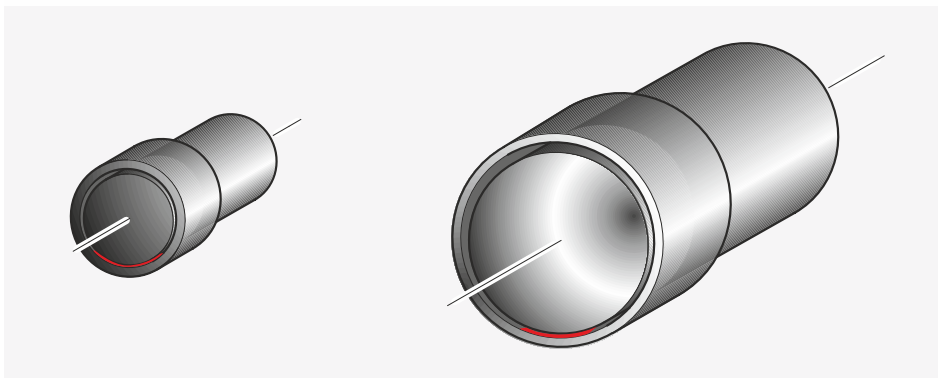


Fig. 12: Contact area between bearing and shaft.

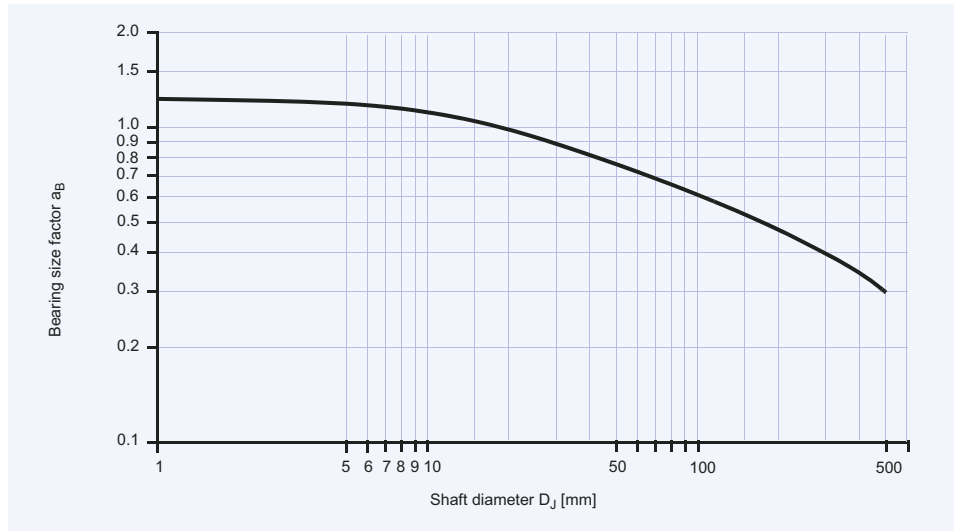


Fig. 13: Bearing size factor  $a_B$

### Bore Burnishing

Burnishing or machining the bore of a DU bearing results in a reduction in the wear performance. The application factor  $a_C$

given in Table 8 is used in the design calculations to allow for this effect.

Degree of sizing		Application factor $a_C$
<b>Burnishing:</b> Excess of burnishing tool diameter over mean bore size	0.025 mm	0.8
	0.038 mm	0.6
	0.050 mm	0.3
<b>Boring:</b> Depth of cut	0.025 mm	0.6
	0.038 mm	0.3
	0.050 mm	0.1

Table 8: Bore burnishing or machining application factor  $a_C$

### Type of Load

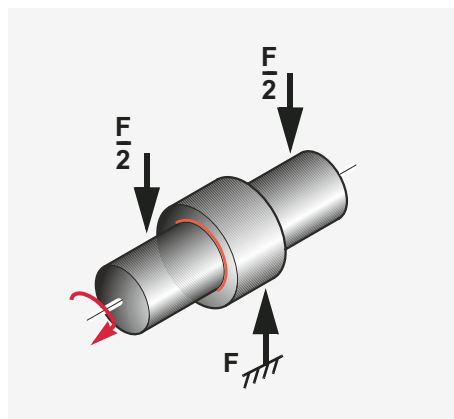


Fig. 14: Steady load, Bush stationary, Shaft rotating

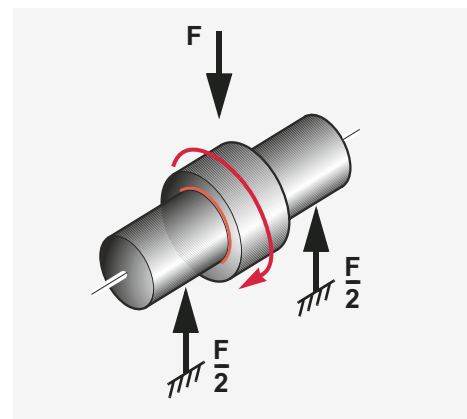


Fig. 15: Rotating load, Shaft stationary, Bush rotating

### 3.7 Calculation of Bearing Size

In designing all bearings, the shaft diameter is usually determined by considerations of physical stability or stiffness and the main variable to be determined is the length of the bush or the land width of the thrust washer.

The formulae given below enable designers to calculate the length or width

necessary to satisfy both the Specific Load Limit and the  $\bar{p}U$ /Life relationship.

If it is found that the total length exceeds twice the diameter of the shaft, this indicates that the conditions envisaged are too severe for DU material and consideration should be given to repositioning the bearings in order to reduce the load.

#### Calculation for Bushes

##### Bush Stationary, Shaft Rotating

$$(3.7.1) \quad B = \frac{F \cdot N \cdot (L_H + a_L)}{1.25 \cdot 10^7 \cdot a_T \cdot a_M \cdot a_B} + \frac{F}{\bar{p}_{lim} \cdot D_i} \quad [\text{mm}]$$

##### Bush Rotating, Shaft Stationary

$$(3.7.2) \quad B = \frac{F \cdot N \cdot (L_H + a_L)}{2.5 \cdot 10^7 \cdot a_T \cdot a_M \cdot a_B} + \frac{F}{\bar{p}_{lim} \cdot D_i} \quad [\text{mm}]$$

#### Calculation for Thrust Washers

$$(3.7.3) \quad D_o - D_i = \frac{F \cdot N \cdot (L_H + a_L)}{1.25 \cdot 10^7 \cdot a_T \cdot a_M \cdot a_B} + \sqrt{D_i^2 + \frac{1.3F}{\bar{p}_{lim}}} - D_i \quad [\text{mm}]$$

#### Calculation for Slideways

$$(3.7.4) \quad A = \frac{2.38 \cdot F \cdot U(L_H + a_L)}{10^3 \cdot a_T \cdot a_M} \cdot \frac{(L + L_S)}{L} + \frac{F}{\bar{p}_{lim}} \quad [\text{mm}^2]$$

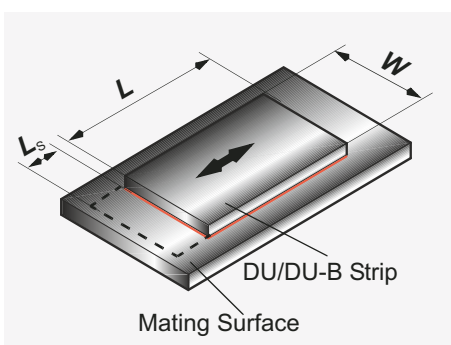


Fig. 16: Slideway

## 3.8 Calculation of Bearing Service Life

Where the size of a bearing is governed largely by the space available the following calculation can be used to determine whether

its useful life will satisfy the requirements. If the calculated life is inadequate, a larger bearing should be considered.

### Specific load $\bar{p}$

#### Bushes

$$(3.8.1) \quad \bar{p} \quad [\text{N/mm}^2]$$

$$\bar{p} = \frac{F}{D_i \cdot B}$$

#### Flanged Bushes

$$(3.8.2) \quad \bar{p} \quad [\text{N/mm}^2]$$

$$\bar{p} = \frac{F}{0.04 \cdot (D_{fl}^2 - D_i^2)}$$

### High load factor $a_E$

$$(3.8.4) \quad a_E \quad [-]$$

$$a_E = \frac{\bar{p}_{lim} - \bar{p}}{\bar{p}_{lim}}$$

$\bar{p}_{lim}$  see Table 4, Page 13

If  $a_E$  is negative then the bearing is overloaded. Increase the bearing diameter and/or length.

### Modified $\bar{p}U$ Factor

#### Bushes

$$(3.8.5) \quad \bar{p}U \quad [\text{N/mm}^2 \times \text{m/s}]$$

$$\bar{p}U = \frac{5.25 \cdot 10^{-5} F \cdot N}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B}$$

#### Flanged Bushes

$$(3.8.6) \quad \bar{p}U \quad [\text{N/mm}^2 \times \text{m/s}]$$

$$\bar{p}U = \frac{6.5 \cdot 10^{-4} F \cdot N}{a_E \cdot (D_{fl} - D_i) \cdot a_T \cdot a_M \cdot a_B}$$

For oscillating movement, calculate the average rotational speed.

$$(3.8.8) \quad N \quad [1/\text{min}]$$

$$N = \frac{4\phi \cdot N_{osz}}{360}$$

#### Thrust Washers

$$(3.8.3) \quad \bar{p} \quad [\text{N/mm}^2]$$

$$\bar{p} = \frac{4F}{\bar{p} \cdot (D_o^2 - D_i^2)}$$

#### Thrust Washers

$$(3.8.7) \quad \bar{p}U \quad [\text{N/mm}^2 \times \text{m/s}]$$

$$\bar{p}U = \frac{3.34 \cdot 10^{-5} F \cdot N}{a_E \cdot (D_o - D_i) \cdot a_T \cdot a_M \cdot a_B}$$

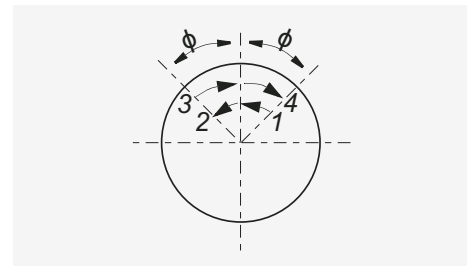


Fig. 17: Oscillating cycle  $\phi$

### Estimation of bearing life $L_H$

#### Bushes (Steady load)

(3.8.9) [h]

$$L_H = \frac{615}{\bar{p}U} a_L$$

#### Bushes (Rotating load)

(3.8.10) [h]

$$L_H = \frac{1230}{\bar{p}U} a_L$$

#### Flanged Bushes (Axial load)

(3.8.11) [h]

$$L_H = \frac{410}{\bar{p}U} a_L$$

#### Thrust Washers

(3.8.12) [h]

$$L_H = \frac{410}{\bar{p}U} a_L$$

### Bore Burnishing

If the DU bush is bore burnished then this must be allowed for in estimating the bea-

ring life by the application factor  $a_C$  (Table 8, Page 16).

### Estimated Bearing Life

(3.8.13) [h]

$$L_H = L_H \cdot a_C$$

### Slideways

#### Specific load factor

(3.8.14) [-]

$$a_{E1} = A - \frac{F}{\bar{p}_{lim}}$$

If negative the bearing is overloaded and the bearing area should be increased.

#### Speed temperature and material application factors

(3.8.15) [-]

$$a_{E2} = \frac{420 \cdot a_T \cdot a_M}{F \cdot U}$$

#### Relative contact area factor

(3.8.16) [-]

$$a_{E3} = \frac{A}{A_M}$$

### Estimated bearing life

(3.8.17) [h]

$$L_H = a_{E1} \cdot a_{E2} \cdot a_{E3} \cdot a_L$$

Estimated bearing lives greater than 4000 h are subject to error due to inaccuracies in the extrapolation of test data.

$Z_T = L_H \times N_{OSZ} \times 60$  (for Oscillating Movements) (3.8.18).

$Z_T = L_H \times C \times 60$  (for dynamic load) (3.8.19).

Check that  $Z_T$  is less than total number of cycles  $Q$  for the operating specific load  $p$  (Table 4, Page 13).

For Oscillating Movements or Dynamic load: Calculate estimated number of cycles  $Z_T$ .

If  $Z_T < Q$ ,  $L_H$  will be limited by wear after  $Z_T$  cycles.

If  $Z_T > Q$ ,  $L_H$  will be limited by fatigue after  $Z_T$  cycles.

## 3.9 Worked Examples

### Cylindrical Bush

Given:			
Load Details	Steady Load	Inside Diameter $D_i$	40 mm
	Continuous Rotation	Length B	30 mm
Shaft	Steel	Bearing Load F	5000 N
	Unlubricated at 25 °C	Rotational Speed N	50 1/min

Calculation Constants and Application Factors			
Specific Load Limit $\bar{p}_{lim}$	140 N/mm <sup>2</sup>	(Table 4, Page 13)	
Temperature Application Factor $a_T$	1.0	(Table 6, Page 14)	
Material Application Factor $a_M$	1.0	(Table 7, Page 15)	
Bearing Size Factor $a_B$	0.85	(Fig. 13, Page 16)	
Life Correction Constant $a_L$	200	(Table 7, Page 15)	

Calculation	Ref	Value
Specific Load $\bar{p}$ [N/mm <sup>2</sup> ]	(3.2.1), Page 12	$\bar{p} = \frac{F}{D_i \cdot B} = \frac{5000}{40 \cdot 30} = 4.17$
Sliding Speed U [m/s]	(3.4.1), Page 13	$U = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3} = \frac{40 \cdot 3.14 \cdot 50}{60 \cdot 10^3} = 0.105$
$\bar{p}U$ Factor (Calculate from Table 5, Page 14)	(3.5.1), Page 14	$\bar{p}U = \bar{p} \cdot U = 4.17 \cdot 0.105 = 0.438$
High Load Factor $a_E$ [-] (must be >0)	(3.8.4), Page 18	$a_E = \frac{\bar{p}_{lim} - \bar{p}}{\bar{p}_{lim}} = \frac{140 - 4.17}{140} = 0.97$
Modified $\bar{p}U$ Factor [N/mm <sup>2</sup> x m/s]	(3.8.5), Page 18	$\bar{p}U = \frac{5.25 \cdot 10^{-5} F \cdot N}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B} = 0.53$
Life $L_H$ [h]	(3.8.9), Page 19	$L_H = \frac{615}{\bar{p}U} \cdot a_L = \frac{615}{0.53} \cdot 200 = 960$

### Cylindrical Bush

Given:			
Load Details	Dynamic Load	Inside Diameter $D_i$	30 mm
	Continuous Rotation	Length B	30 mm
Shaft	Steel	Bearing Load F	25000 N
	Unlubricated at 25 °C	Rotational Speed N	15 1/min

Calculation Constants and Application Factors			
Specific Load Limit $\bar{p}_{lim}$	60 N/mm <sup>2</sup>	(Table 4, Page 13)	
Temperature Application Factor $a_T$	1.0	(Table 6, Page 14)	
Material Application Factor $a_M$	1.0	(Table 7, Page 15)	
Bearing Size Factor $a_B$	1	(Fig. 13, Page 16)	
Life Correction Constant $a_L$	200	(Table 7, Page 15)	

Calculation	Ref	Value
Specific Load $\bar{p}$ [N/mm <sup>2</sup> ]	(3.2.1), Page 12	$\bar{p} = \frac{F}{D_i \cdot B} = \frac{25000}{30 \cdot 30} = 27.78$
Sliding Speed U [m/s]	(3.4.1), Page 13	$U = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3} = \frac{30 \cdot 3.14 \cdot 15}{60 \cdot 10^3} = 0.024$
$\bar{p}U$ Factor (Calculate from Table 5, Page 14)	(3.5.1), Page 14	$\bar{p}U = \bar{p} \cdot U = 27.78 \cdot 0.024 = 0.669$
High Load Factor $a_E$ [-] (must be >0)	(3.8.4), Page 18	$a_E = \frac{\bar{p}_{lim} - \bar{p}}{\bar{p}_{lim}} = \frac{60 - 27.78}{60} = 0.54$
Modified $\bar{p}U$ Factor [N/mm <sup>2</sup> x m/s]	(3.8.5), Page 18	$\bar{p}U = \frac{5.25 \cdot 10^{-5} F \cdot N}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B} = 1.23$
Life $L_H$ [h]	(3.8.9), Page 19	$L_H = \frac{615}{\bar{p}U} \cdot a_L = \frac{615}{1.23} \cdot 200 = 350$
Calculate total load cycles	Table 4, Page 13	$Z_T = 300 \cdot 60 \cdot 60 = 300 \cdot 10^6$ Q for 27.78 N/mm <sup>2</sup> = bearing will fatigue after 10 <sup>5</sup> cycles (= 28 h)

### Cylindrical Bush

Given:			
Load Details	Steady Load Load Rotating	Inside Diameter $D_i$	50 mm
	Continuous Rotation	Length B	50 mm
Shaft	Steel	Bearing Load F	10000 N
	Unlubricated at 100 °C	Rotational Speed N	50 1/min

Calculation Constants and Application Factors			
Specific Load Limit $\bar{p}_{lim}$	60 N/mm <sup>2</sup>	(Table 4, Page 13)	
Temperature Application Factor $a_T$	0.6	(Table 6, Page 14)	
Material Application Factor $a_M$	1.0	(Table 7, Page 15)	
Bearing Size Factor $a_B$	0.78	(Fig. 13, Page 16)	
Life Correction Constant $a_L$	200	(Table 7, Page 15)	

Calculation	Ref	Value
Specific Load $\bar{p}$ [N/mm <sup>2</sup> ]	(3.2.1), Page 12	$\bar{p} = \frac{F}{D_i \cdot B} = \frac{10000}{50 \cdot 50} = 4.0$
Sliding Speed U [m/s]	(3.4.1), Page 13	$U = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3} = \frac{50 \cdot 3.14 \cdot 50}{60 \cdot 10^3} = 0.131$
$\bar{p}U$ Factor (Calculate from Table 5, Page 14)	(3.5.1), Page 14	$\bar{p}U = \bar{p} \cdot U = 4.0 \cdot 0.131 = 0.542$
High Load Factor $a_E$ [-] (must be >0)	(3.8.4), Page 18	$a_E = \frac{\bar{p}_{lim} - \bar{p}}{\bar{p}_{lim}} = \frac{60 - 4.0}{60} = 0.93$
Modified $\bar{p}U$ Factor [N/mm <sup>2</sup> x m/s]	(3.8.5), Page 18	$\bar{p}U = \frac{5.25 \cdot 10^{-5} F \cdot N}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B} = 1.20$
Life $L_H$ [h]	(3.8.9), Page 19	$L_H = \frac{1230}{\bar{p}U} \cdot a_L = \frac{1230}{1.20} \cdot 200 = 825$

### Cylindrical Bush

Given:			
Load Details	Steady Load	Inside Diameter $D_i$	45 mm
	Oscillating Movements	Length B	40 mm
Shaft	Stainless Steel	Bearing Load F	40000 N
	Unlubricated at 25 °C	Frequency C	150
	Continuous operation	Amplitudes $\phi$	20 °

Calculation Constants and Application Factors			
Specific Load Limit $\bar{p}_{lim}$	140 N/mm <sup>2</sup>	(Table 4, Page 13)	
Temperature Application Factor $a_T$	1.0	(Table 6, Page 14)	
Material Application Factor $a_M$	2.0	(Table 7, Page 15)	
Bearing Size Factor $a_B$	0.81	(Fig. 13, Page 16)	
Life Correction Constant $a_L$	200	(Table 7, Page 15)	

Calculation	Ref	Value
Specific Load $\bar{p}$ [N/mm <sup>2</sup> ]	(3.2.1), Page 12	$\bar{p} = \frac{F}{D_i \cdot B} = \frac{40000}{45 \cdot 40} = 22.22$
Sliding Speed U [m/s]	(3.4.1), Page 13	$U = \frac{45 \cdot 3.14 \cdot 33.33}{60 \cdot 10^3} = 0.078$
Average speed N [1/min]	(3.8.8), Page 18	$N = \frac{4\phi N_{osz}}{360} = \frac{4 \cdot 20 \cdot 150}{360} = 33.33$
$\bar{p}U$ Factor (Calculate from Table 5, Page 14)	(3.5.1), Page 14	$\bar{p}U = \bar{p} \cdot U = 22.22 \cdot 0.078 = 1.733$
High Load Factor $a_E$ [-] (must be >0)	(3.8.4), Page 18	$a_E = \frac{\bar{p}_{lim} - \bar{p}}{\bar{p}_{lim}} = \frac{140 - 22.22}{140} = 0.84$
Modified $\bar{p}U$ Factor [N/mm <sup>2</sup> x m/s]	(3.8.5), Page 18	$\bar{p}U = \frac{5.25 \cdot 10^{-5} F \cdot N}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B} = 1.29$
Life $L_H$ [h]	(3.8.9), Page 19	$L_H = \frac{615}{\bar{p}U} \cdot a_L = \frac{615}{1.29} \cdot 200 = 277$
Calculate total load cycles	Table 4, Page 13	$Z_T = 277 \cdot 150 \cdot 60 = 2.5 \cdot 10^6$ Q for 22.22 N/mm <sup>2</sup> = 10 <sup>8</sup> bearing o.k.!



## Thrust Washer

Given:			
Load Details	Axial Load,	Outside Diameter $D_o$	62 mm
	Continuous Rotation	Inside Diameter $D_i$	38 mm
Shaft	Steel	Bearing Load F	6500 N
	Unlubricated at 25 °C	Rotational Speed N	60 1/min

### Calculation Constants and Application Factors

Specific Load Limit $\bar{p}_{lim}$	140 N/mm <sup>2</sup>	(Table 4, Page 13)
Temperature Application Factor $a_T$	1.0	(Table 6, Page 14)
Material Application Factor $a_M$	1.0	(Table 7, Page 15)
Bearing Size Factor $a_B$	0.85	(Fig. 13, Page 16)
Life Correction Constant $a_L$	200	(Table 7, Page 15)

Calculation	Ref	Value
Specific Load $\bar{p}$ [N/mm <sup>2</sup> ]	(3.8.3), Page 18	$\bar{p} = \frac{4 \cdot 6500}{3.14 \cdot (62^2 - 38^2)} = 3.45$
Sliding Speed U [m/s]	(3.4.2), Page 13	$U = \frac{(62+38) \cdot 3.14 \cdot 60}{2 \cdot 60 \cdot 1000} = 0.157$
$\bar{p}U$ Factor (Calculate from Table 5, Page 14)	(3.5.1), Page 14	$\bar{p}U = \bar{p} \cdot U = 3.45 \cdot 0.157 = 0.541$
High Load Factor $a_E$ [-]	(3.8.4), Page 18	$a_E = \frac{140 - 3.45}{140} = 0.98$
Modified $\bar{p}U$ Factor [N/mm <sup>2</sup> x m/s]	(3.8.7), Page 18	$\bar{p}U = \frac{3.34 \cdot 10^{-5} \cdot 6500 \cdot 60}{0.87 \cdot (62 - 38) \cdot 1 \cdot 1 \cdot 0.85} = 0.65$
Life $L_H$ [h]	(3.8.12), Page 19	$L_H = \frac{410}{0.65} \cdot 200 = 431$

## Flanged Bush

Given:			
Load Details	Axial Load	Flange outside Diameter $D_{fl}$	23 mm
	Continuous Rotation	Inside Diameter $D_i$	15 mm
Shaft	Steel	Bearing Load F	250 N
	Unlubricated at 25 °C	Rotational Speed N	25 1/min


### Calculation Constants and Application Factors

Specific Load Limit $\bar{p}_{lim}$	140 N/mm <sup>2</sup>	(Table 4, Page 13)
Temperature Application Factor $a_T$	1.0	(Table 6, Page 14)
Material Application Factor $a_M$	1.0	(Table 7, Page 15)
Bearing Size Factor $a_B$	1.0	(Fig. 13, Page 16)
Life Correction Constant $a_L$	200	(Table 7, Page 15)

Calculation	Ref	Value
Specific Load $\bar{p}$ [N/mm <sup>2</sup> ]	(3.2.2), Page 12	$\bar{p} = \frac{250}{0.04 \cdot (23^2 - 15^2)} = 20.55$
Sliding Speed U [m/s]	(3.4.2), Page 13	$U = \frac{(23+15) \cdot 3.14 \cdot 25}{2 \cdot 60 \cdot 1000} = 0.025$
$\bar{p}U$ Factor (Calculate from Table 5, Page 14)	(3.5.1), Page 14	$\bar{p}U = \bar{p} \cdot U = 20.55 \cdot 0.025 = 0.513$
High Load Factor $a_E$ [-]	(3.8.4), Page 18	$a_E = \frac{140 - 20.55}{140} = 0.85$
Modified $\bar{p}U$ Factor [N/mm <sup>2</sup> x m/s]	(3.8.6), Page 18	$\bar{p}U = \frac{6.5 \cdot 10^{-5} \cdot 250 \cdot 50}{0.85 \cdot (23 - 15) \cdot 1 \cdot 1 \cdot 1} = 0.59$
Life $L_H$ [h]	(3.8.11), Page 19	$L_H = \frac{410}{0.59} \cdot 200 = 495$

# 4 Data Sheet Application: \_\_\_\_\_

## 4.1 Data for bearing design calculations

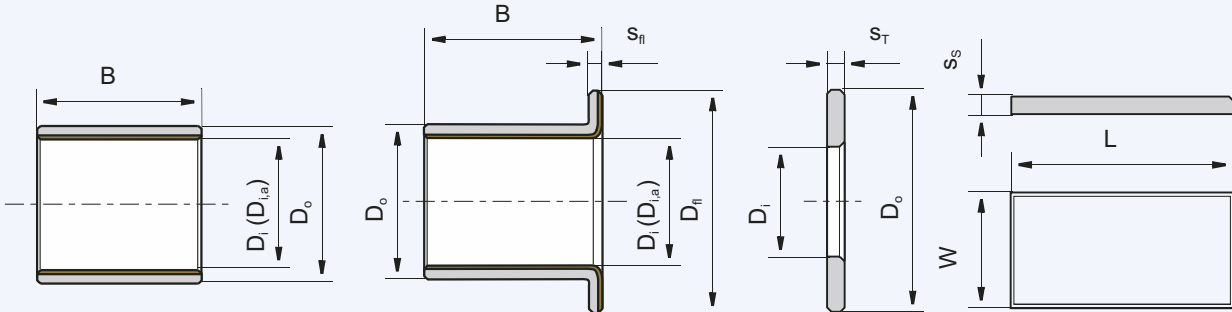

- Cylindrical Bush   
  Flanged Bush   
  Thrust Washer   
  Slideplate   
  Special (Sketch)
- Rotational movement   
  Steady load   
  Rotating load   
  Oscillating movement   
  Linear movement

- Existing Design   
  New Design

Quantity

**Dimensions in mm**

Inside Diameter	$D_i$	<input type="text"/>
Outside Diameter	$D_o$	<input type="text"/>
Length	$B$	<input type="text"/>
Flange Diameter	$D_f$	<input type="text"/>
Flange Thickness	$S_f$	<input type="text"/>
Length of slideplate	$L$	<input type="text"/>
Width of slideplate	$W$	<input type="text"/>
Thickness of slideplate	$S_s$	<input type="text"/>

**Load**

Radial load or specific load  $F$  [N]   
 $\bar{p}$  [N/mm<sup>2</sup>]

Axial load or specific load  $F$  [N]   
 $\bar{p}$  [N/mm<sup>2</sup>]

**Movement**

Rotational speed	$N$ [1/min]	<input type="text"/>
Speed	$U$ [m/s]	<input type="text"/>
Length of Stroke	$L_s$ [mm]	<input type="text"/>
Frequency of Stroke	[1/min]	<input type="text"/>
Oscillating cycle	$\phi$ [°]	<input type="text"/>
Oscillating frequency	$N_{osz}$ [1/min]	<input type="text"/>

**Service hours per day**

Continuous operation	<input type="text"/>
Intermittent operation	<input type="text"/>
Operating time	<input type="text"/>
Days per year	<input type="text"/>

**Fits and Tolerances**

Shaft  $D_J$    
 Bearing Housing  $D_H$

**Operating Environment**

Ambient temperature  $T_{amb}$  [°]

Housing with good heat transfer properties

Light pressing or insulated housing which poor heat transfer properties

Non metal housing with poor heat transfer properties

Alternate operation in water and dry

**Mating surface**

Material

Hardness  $HB/HRC$

Surface finish  $R_a$  [ $\mu m$ ]

**Lubrication**

Dry

Continuous lubrication

Process fluid lubrication

Initial lubrication only

Hydrodynamic conditions

Process Fluid

Lubricant

Dynamic viscosity  $\eta$

**Service life**

Required service life  $L_H$  [h]

Customer Data  
 Company: City:  
 Street: Post Code:

Project:  
 Name:  
 Tel.:

Date:  
 Signature:  
 Fax:

## 5 Lubrication

Although DU was developed as a dry self lubricating bearing material, DU also provides excellent performance in lubricated applications.

### 5.1 Lubricants

DU can be used with most fluids including

- water
- lubricating oils
- engine oil
- turbine oil
- hydraulic fluid
- solvent
- refrigerants

In general, the fluid will be acceptable if it does not chemically attack the PTFE/lead overlay or the porous bronze interlayer. Where there is doubt about the suitability of a fluid, a simple test is to submerge a

The following sections describe the basics of lubrication and provide guidance on the application of DU in such environments.

sample of DU material in the fluid for two to three weeks at 15-20 °C above the operating temperature.

The following will usually indicate that the fluid is not suitable for use with DU:

- A significant change in the thickness of the DU material,
- A visible change in the bearing surface other than some discolouration or staining
- A visible change in the microstructure of the bronze interlayer

### 5.2 Tribology

There are three modes of lubricated bearing operation which relate to the thickness of the developed lubricant film between the bearing and the mating surface.

These three modes of operation depend upon:

- Bearing dimensions
- Clearance
- Load
- Speed
- Lubricant Viscosity
- Lubricant Flow

#### Hydrodynamic lubrication

##### Characterised by:

- Complete separation of the shaft from the bearing by the lubricant film
- Very low friction and no wear of the bearing or shaft since there is no contact.
- Coefficients of friction of 0.001 to 0.01

Hydrodynamic conditions occur when

$$(5.2.1) \quad \bar{p} \leq \frac{U \cdot \eta}{7.5} \cdot \frac{B}{D_i} \quad [\text{N/mm}^2]$$

$$\bar{p} \leq \frac{U \cdot \eta}{7.5} \cdot \frac{B}{D_i}$$

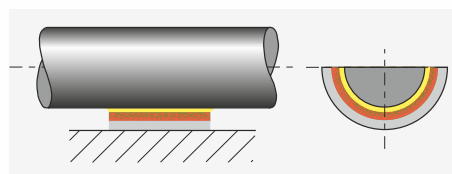


Fig. 18: Hydrodynamic lubrication

## Mixed film lubrication

### Characterised by:

- Combination of hydrodynamic and boundary lubrication.
- Part of the load is carried by localised areas of self pressurised lubricant and the remainder supported by boundary lubrication.
- Friction and wear depend upon the degree of hydrodynamic support developed.

- DU provides low friction and high wear resistance to support the boundary lubricated element of the load.

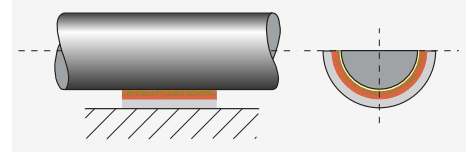


Fig. 19: Mixed film lubrication

## Boundary lubrication

### Characterised by:

- Rubbing of the shaft against the bearing with virtually no lubricant separating the two surfaces.
- Bearing material selection is critical to performance
- Shaft wear is likely due to contact between bearing and shaft.
- The excellent self lubricating properties of DU material minimises wear under these conditions.

- The coefficient of friction with DU is typically 0.02 to 0.06 under boundary lubrication conditions.

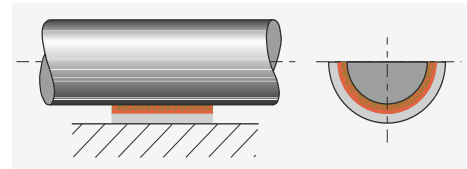


Fig. 20: Boundary lubrication

## 5.3 Characteristics of Lubricated DU bearings

DU is particularly effective in the most demanding of lubricated applications

where full hydrodynamic operation cannot be maintained, for example:

### • High load conditions

In highly loaded applications operating under boundary or mixed film conditions DU shows excellent wear resistance and low friction.

### • Start up and shut down under load

With insufficient speed to generate a hydrodynamic film the bearing will operate under boundary or mixed film conditions. DU minimises wear and requires less start up torque than conventional metallic bearings.

### • Sparse lubrication

Many applications require the bearing to operate with less than the ideal lubricant supply, typically with splash or mist lubrication only. DU provides excellent self lubricating properties.

### • Dry operation after running in water

If a DU bearing is required to run dry after running in water under non hydrodynamic conditions then the wear resistance will be substantially reduced due to an increased amount of bedding in wear.

## 5.4 Design Guidance for Lubricated Applications

Fig. 21 shows the three lubrication regimes discussed above. In order to use Fig. 21, using the formula on page 12 and page 13:

- Calculate the specific load  $\bar{p}$ ,
- Calculate the shaft surface speed  $U$ .

Using the viscosity temperature relationships presented in Table 9.

- Determine the lubricant viscosity in centipoise, of the lubricant.

If the operating temperature of the fluid is unknown, a provisional temperature of 25 °C above ambient can be used.

**Area 1**

The bearing will operate with boundary lubrication and pU factor will be the major determinant of bearing life. The DU bearing performance can be calculated using

**Area 2**

The bearing will operate with mixed film lubrication and the pU factor is no longer a significant parameter in determining the

**Area 3**

The bearing will operate with hydrodynamic lubrication. The bearing wear will be determined only by the cleanliness of the

**Area 4**

These are the most demanding operating conditions. The bearing is operated under either high speed or high bearing load to viscosity ratio, or a combination of both.

These conditions may cause:

the method given in Section 3, although the result will probably underestimate the bearing life

bearing life. The DU bearing performance will depend upon the nature of the fluid and the actual service conditions.

lubricant and the frequency of start up and shut down.

- excessive operating temperature and/or
- high wear rate.

The bearing performance may be improved by adding one or more grooves to the bearing and a shaft surface finish <math><0.05 \mu\text{m } R\_a</math>.

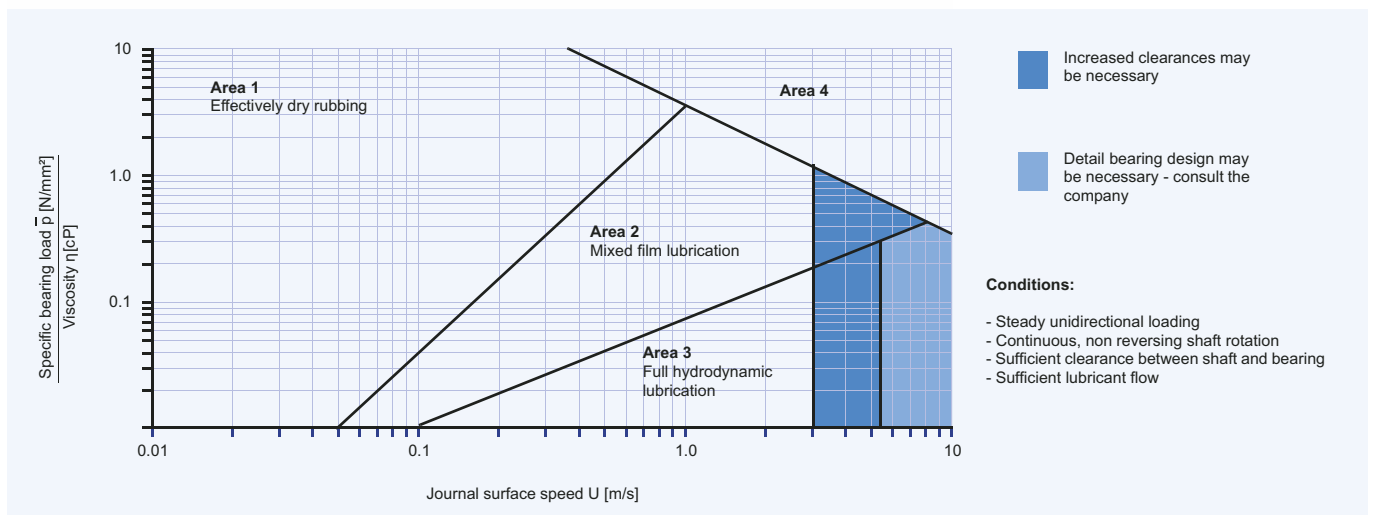


Fig. 21: Design guide for lubricated application

Temperature [°C]	Viscosity cP														
	0	10	20	30	40	50	60	70	80	90	100	110	120	130	140
<b>Lubricant</b>															
ISO VG 32	310	146	77	44	27	18	13	9.3	7.0	5.5	4.4	3.6	3.0	2.5	2.2
ISO VG 46	570	247	121	67	40	25	17	12	9.0	6.9	5.4	4.4	3.6	3.0	2.6
ISO VG 68	940	395	190	102	59	37	24	17	12	9.3	7.2	5.8	4.7	3.9	3.3
ISO VG 100	2110	780	335	164	89	52	33	22	15	11.3	8.6	6.7	5.3	4.3	3.6
ISO VG 150	3600	1290	540	255	134	77	48	31	21	15	11	8.8	7.0	5.6	4.6
Diesel oil	4.6	4.0	3.4	3.0	2.6	2.3	2.0	1.7	1.4	1.1	0.95				
Petrol	0.6	0.56	0.52	0.48	0.44	0.40	0.36	0.33	0.31						
Kerosene	2.0	1.7	1.5	1.3	1.1	0.95	0.85	0.75	0.65	0.60	0.55				
Water	1.79	1.30	1.0	0.84	0.69	0.55	0.48	0.41	0.34	0.32	0.28				

Table 9: Viscosity data

## 5.5 Clearances for lubricated operation

The recommended shaft and housing diameters given for standard DU bushes will provide sufficient clearance for applications operating with boundary lubrication.

For bearings operating with mixed film or hydrodynamic lubrication it may be neces-

sary to improve the fluid flow through the bearing by reducing the recommended shaft diameter by approximately 0.1%, particularly when the shaft surface speed exceeds 2.5 m/s.

## 5.6 Mating Surface Finish for lubricated operation

- $R_a \leq 0.4 \mu\text{m}$  Boundary lubrication
- $R_a = 0.1\text{-}0.2 \mu\text{m}$  Mixed film or hydrodynamic conditions
- $R_a \leq 0.05 \mu\text{m}$  for the most demanding operating conditions

## 5.7 Grooving for lubricated operation

In demanding applications an axial oil groove will improve the performance of DU. Fig. 22 shows the recommended form and location of a single groove with

respect to the applied load and the bearing split. GGB can manufacture special DU bearings with embossed or milled grooves on request.

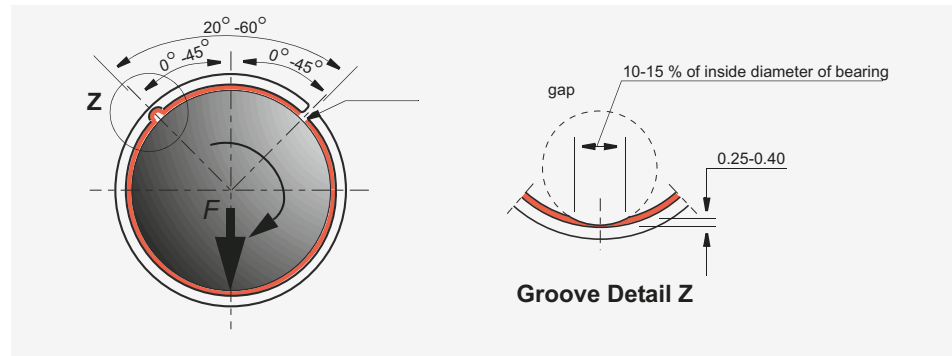


Fig. 22: Location of oil holes and grooves

## 5.8 Grease Lubrication

DU is not generally recommended for use with grease lubrication. In particular the following must be avoided:

- Dynamic loads - which can result in erosion of the PTFE/lead bearing surface.

- Greases with EP additives or fillers such as graphite or  $\text{MoS}_2$  which can cause rapid wear of DU.



# 6 Bearing Assembly

## Dimensions and Tolerances

DU bushes are prefinished in the bore, and except in very exceptional circumstances, must not be burnished, broached or otherwise modified. It is essential that the correct running clearance is used and that both the diameter of the shaft and the bore of the housing are finished to the limits given in the tables. Under dry running conditions any increase in the clearances given will result in a proportional reduction in performance.

If the bearing housing is unusually flexible the bush will not close in by the calculated

amount and the running clearance will be more than the optimum. In these circumstances the housing should be bored slightly undersize or the journal diameter increased, the correct size being determined by experiment.

Where free running is essential, or where light loads (less than 0.1 N/mm<sup>2</sup>) prevail and the available torque is low, increased clearance is required and it is recommended that the shaft size quoted in the table be reduced by 0.025 mm.

### 6.1 Allowance for Thermal Expansion

For operation in high temperature environments the clearance should be increased by the amounts indicated by Fig. 23 to

compensate for the inward thermal expansion of the bearing lining.

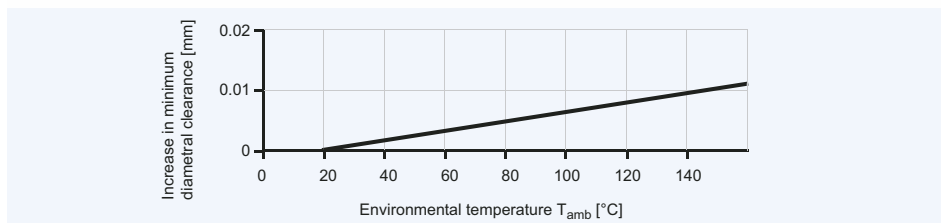


Fig. 23: Increase in diametral clearance

If the housing is non-ferrous then the bore should be reduced by the amounts given in Table 10, in order to give an increased

interference fit to the bush, with a similar reduction in the journal diameter additional to that indicated by Fig. 23.

Housing material	Reduction in housing diameter per 100 °C rise	Reduction in shaft diameter per 100 °C rise
Aluminium alloys	0.1 %	0.1 % + values from Fig. 23
Copper base alloys	0.05 %	0.05 % + values from Fig. 23
Steel and cast iron	–	values from Fig. 23
Zinc base alloys	0.15 %	0.15 % + values from Fig. 23

Table 10: Allowance for high temperature

### 6.2 Tolerances for minimum clearance

Where it is required to keep the variation of assembled clearance to a minimum, closer tolerances can be specified towards the upper end of the journal tolerance and the lower end of the housing tolerance.

If housings to H6 tolerance are used, then the journals should be finished to the following limits.

The sizes in Table 11 give the following nominal clearance range.

$D_i$	$D_j$
<25 mm	-0.019 to -0.029
>25 mm < 50 mm	-0.021 to -0.035

Table 11: Shaft tolerances for use with H6 housings

$D_i$	$C_D$
10 mm	0.005 to 0.078
50 mm	0.005 to 0.130

Table 12: Clearance vs bearing diameter

Sizing

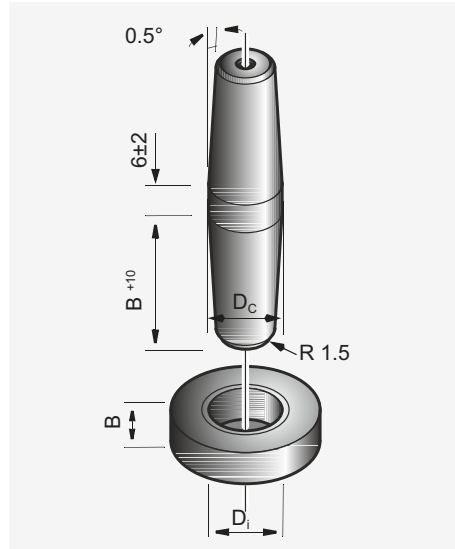


Fig. 24: Burnishing tool

The burnishing or fine boring of the bore of an assembled DU bush in order to achieve a smaller clearance tolerance is only permissible if a substantial reduction in performance is acceptable. Fig. 24 shows a recommended burnishing tool for the sizing of DU bushes.

The coining section of the burnishing tool should be case hardened (case depth 0.6-1.2 mm, HRC 60±2) and polished ( $R_z \approx 1 \mu\text{m}$ ).

Note: Ball burnishing of DU bushes is not recommended.

Assembled bush Inside- $\varnothing$	Required bush Inside- $\varnothing$	Required burnishing tool diameter $D_c$
$D_{i,a}$	$D_{i,a} + 0.025$	$D_{i,a} + 0.06$
$D_{i,a}$	$D_{i,a} + 0.038$	$D_{i,a} + 0.08$
$D_{i,a}$	$D_{i,a} + 0.050$	$D_{i,a} + 0.1$

Table 13: Burnishing tool tolerances

The values given in Table 13 indicate the dimensions of the burnishing tool required to give specific increases in the bearing bore diameter.

Exact values must be determined by test.

The reduction in bearing performance as a result of burnishing is allowed for in the bearing life calculation by the application factor  $a_c$  (Table 8, Page 16).

6.3 Counterface Design

The suitability of mating surface materials and recommendations of mating surface finish for use with DU are discussed in detail on page 15.

DU is normally used in conjunction with ferrous journals and thrust faces, but in damp or corrosive surroundings, particularly without the protection of oil or grease, stainless steel, hard chromium plated mild steel, or hard anodised aluminium is recommended. When plated mating surfaces are specified the plating should possess adequate strength and adhesion, particularly if the bearing is to operate with high fluctuating loads.

The shaft or thrust collar used in conjunction with the DU bush or thrust washer must extend beyond the bearing surface in order to avoid cutting into it. The mating surface must also be free from grooves or flats, the end of the shaft should be given a lead-in chamfer and all sharp edges or projections which may damage the soft overlay of the DU must be removed.

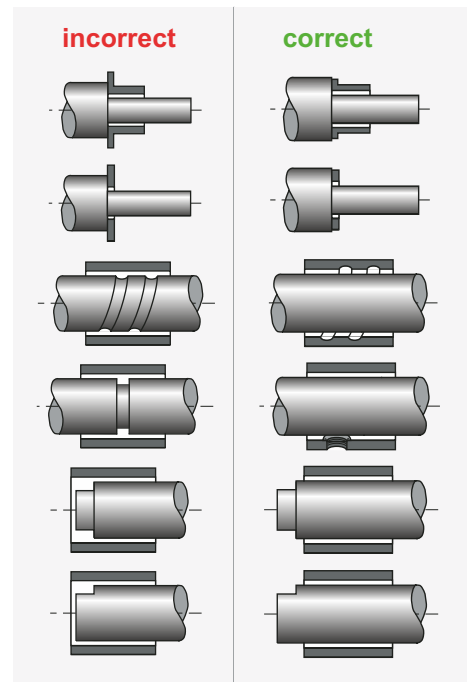


Fig. 25: Counterface Design

## 6.4 Installation

### Fitting of cylindrical bushes

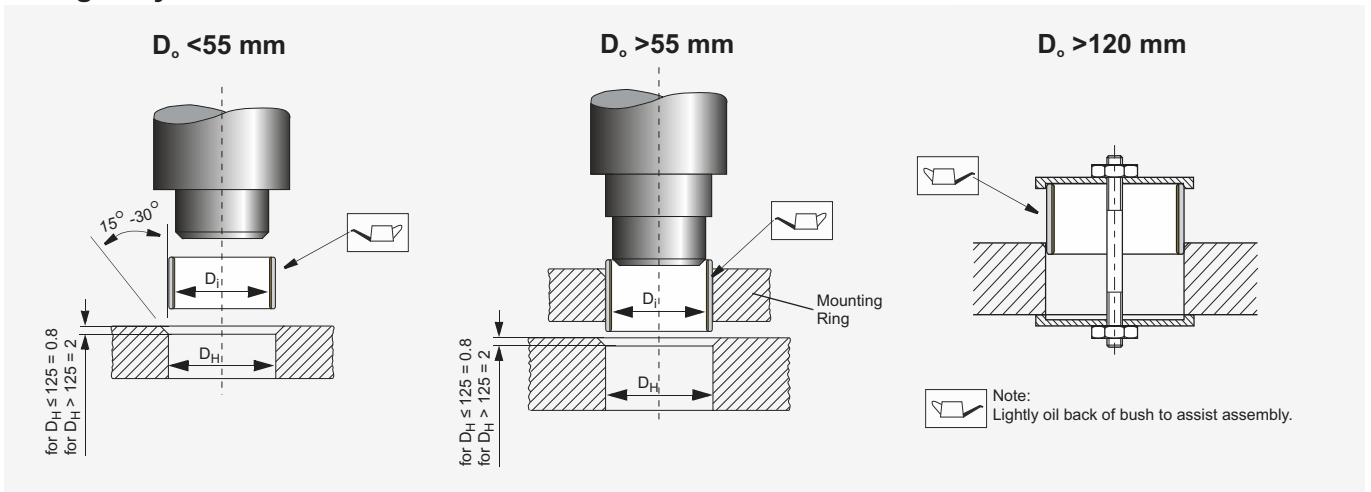


Fig. 26: Fitting of cylindrical bushes

### Fitting of flanged bushes

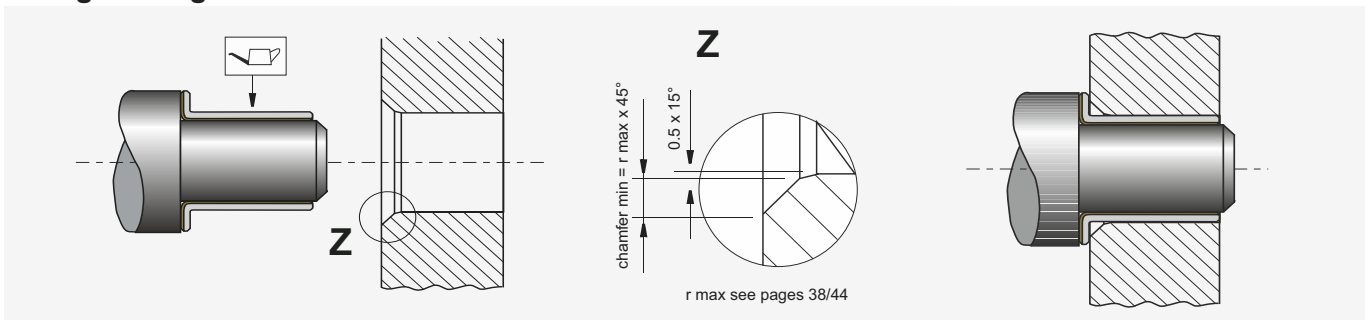


Fig. 27: Fitting of flanged bushes

### Insertion Forces

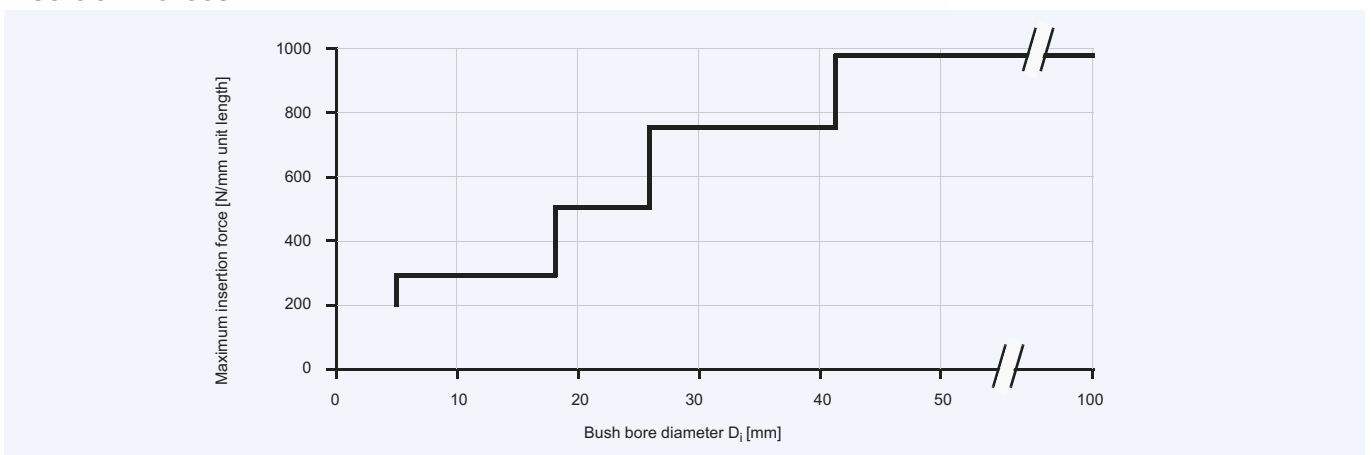


Fig. 28: Maximum Insertion Force

## Alignment

Accurate alignment is an important consideration for all bearing assemblies, but is particularly so for dry bearings because there is no lubricant to spread the load.

With DU bearings misalignment over the length of a bush (or pair of bushes), or over the diameter of a thrust washer should not exceed 0.020 mm as illustrated in Fig. 29.

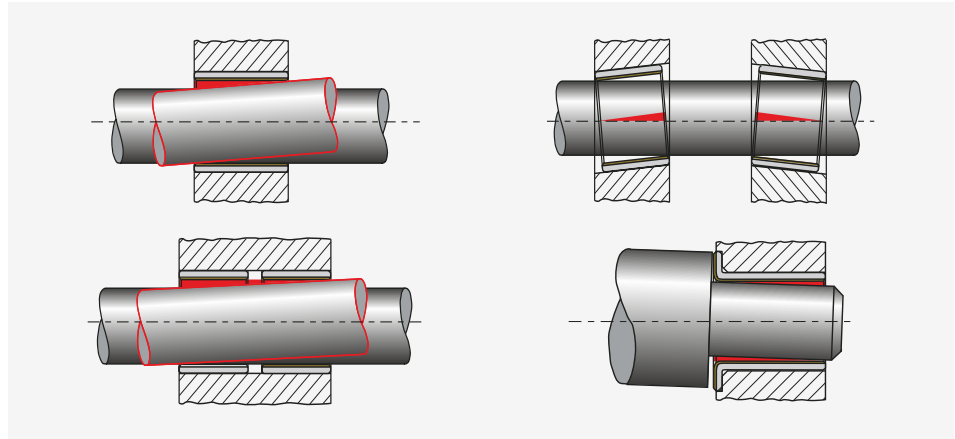


Fig. 29: Alignment

## Sealing

While DU can tolerate the ingress of some contaminant materials into the bearing without loss of performance, where there is the possibility of highly abrasive material

entering the bearing, a suitable sealing arrangement, as illustrated in Fig. 30 should be provided.

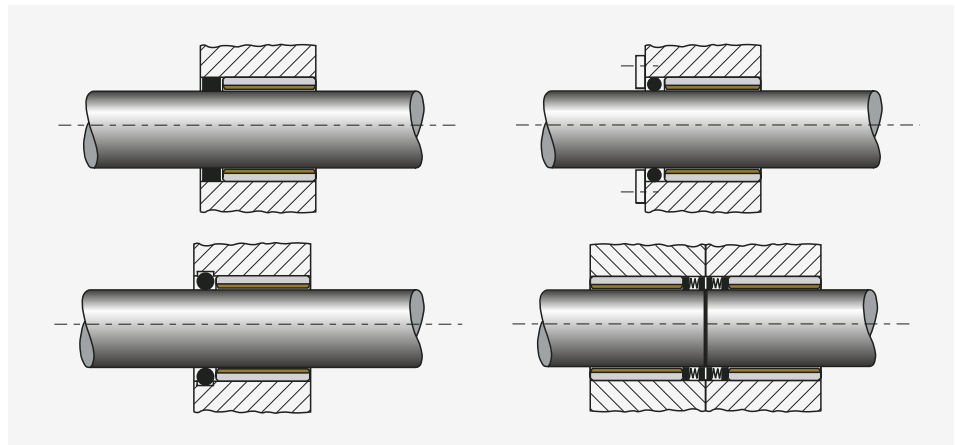


Fig. 30: Recommended sealing arrangements

## 6.5 Axial Location

Where axial location is necessary, it is advisable to fit DU thrust washers in con-

junction with DU bushes, even when the axial loads are low.

### Fitting of Thrust Washers

DU thrust washers should be located in a recess as shown in Fig. 31. The recess diameter should be 0.125 mm larger than the washer diameter and the depth as given in the product tables.

If a recess is not possible one of the following methods may be used:

- Two dowel pins
- Two screws
- Adhesive
- Soldering

### Important Note

- Ensure the washer ID does not touch the shaft after assembly
- Ensure that the washer is mounted with the steel backing to the housing
- Dowel pins should be recessed 0.25 mm below the bearing surface
- Screws should be countersunk 0.25 mm below the bearing surface
- DU must not be heated above 320 °C
- Contact adhesive manufacturers for guidance selection of suitable adhesives
- Protect the bearing surface to prevent contact with adhesive

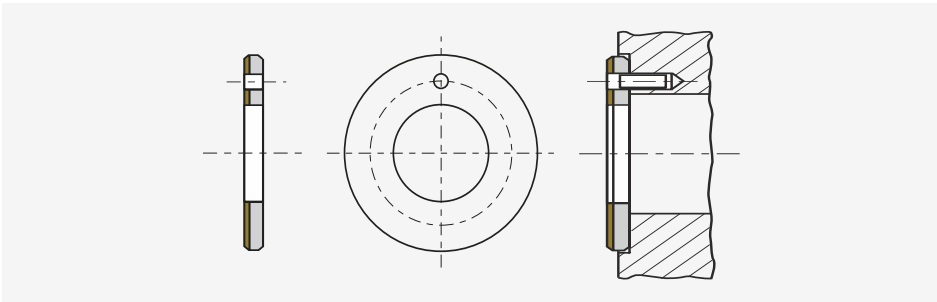


Fig. 31: Installation of Thrust-Washer

### Grooves for Wear Debris Removal

Tests with thrust washers have demonstrated that for optimum dry wear performance at specific loads in excess of 35 N/mm<sup>2</sup>, four wear debris removal grooves should

be machined in the bearing surface as shown in Fig. 32.

Grooves in bushes have not been found to be beneficial in this respect.

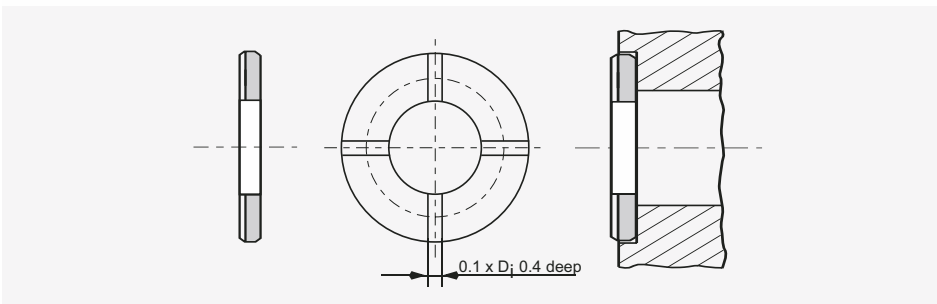


Fig. 32: Debris removal Grooves

### Slideways

DU strip material for use as slideway bearings should be installed using one of the following methods:

- Countersunk screws
- Adhesives
- Mechanical location as shown in Fig. 33

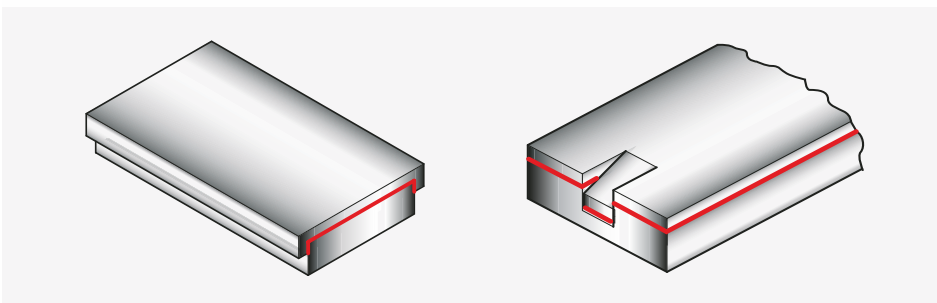


Fig. 33: Mechanical location of DU slideplates

# 7 Modification

## 7.1 Cutting and Machining

The modification of DU bearing components requires no special procedures. In general it is more satisfactory to perform machining or drilling operations from the PTFE side in order to avoid burrs. When cutting is done from the steel side, the

minimum cutting pressure should be used and care taken to ensure that any steel or bronze particles protruding into the remaining bearing material, and all burrs, are removed.

### Drilling Oil Holes

Bushes should be adequately supported during the drilling operation to ensure that

no distortion is caused by the drilling pressure.

### Cutting Strip Material

DU strip material may be cut to size by any one of the following methods.

Care must be taken to protect the bearing surface from damage and to ensure that no deformation of the strip occurs:

- Using side and face cutter, or slitting saw, with the strip held flat and securely

on a horizontal milling machine.

- Cropping
- Guillotine (For widths less than 90 mm only)
- Water-jet cutting
- Laser cutting (see Health Warning)

## 7.2 Electroplating

### DU Components

In order to provide some protection in mildly corrosive environments the steel back and end faces of standard range DU bearings are tin flashed.

If exposed to corrosive liquids further protection should be provided and in very corrosive conditions DU-B should be considered.

DU can be electroplated with most of the conventional electroplating metals including the following:

- zinc ISO 2081-2
- cadmium ISO 2081-2
- nickel ISO 1456-8
- hard chromium ISO 1456-8

For the harder materials if the specified plating thickness exceeds approximately 5  $\mu\text{m}$  then the housing diameter should be increased by twice the plating thickness in order to maintain the correct assembled bearing bore size.

With light deposits of materials such as cadmium, no special precautions are necessary. Harder materials such as nickel however, may strike through the PTFE/lead surface layer of DU and it is advisable to use an appropriate method of masking the bearing surface.

Where electrolytic attack is possible tests should be conducted to ensure that all the materials in the bearing environment are mutually compatible.

### Mating Surfaces


DU can be used against some plated materials as indicated on page 15.

Care should be taken to ensure that the recommended shaft sizes and surface finish are achieved after the plating process.



# 8 Standard Products

## 8.1 DU Cylindrical Bushes

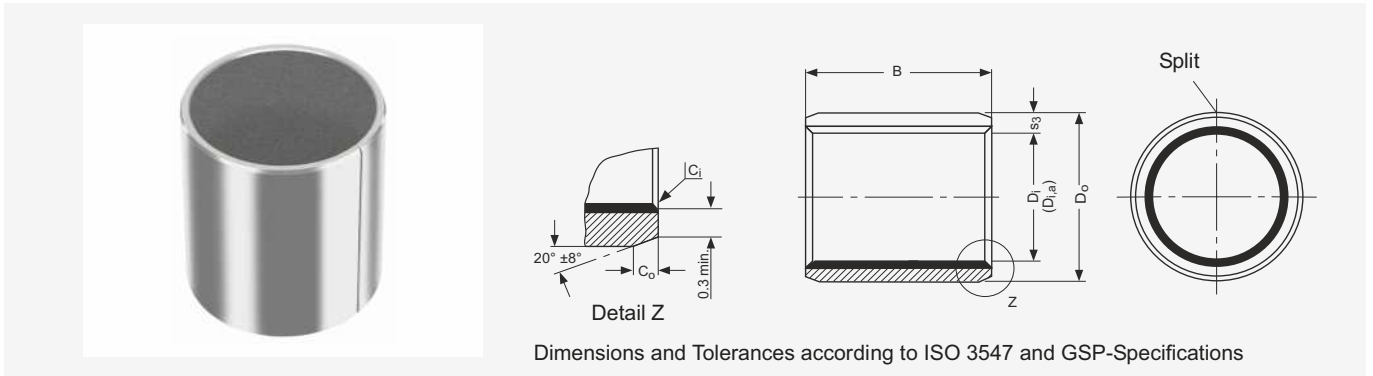

Dimensions and Tolerances according to ISO 3547 and GSP-Specifications

All dimensions in mm

### Outside C<sub>o</sub> and Inside C<sub>i</sub> chamfers

Wall thickness s <sub>3</sub>	C <sub>o</sub> (a)		C <sub>i</sub> (b)
	machined	rolled	
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7

Wall thickness s <sub>3</sub>	C <sub>o</sub> (a)		C <sub>i</sub> (b)
	machined	rolled	
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

a = Chamfer C<sub>o</sub> machined or rolled at the opinion of the manufacturer

b = C<sub>i</sub> can be a radius or a chamfer in accordance with ISO 13715

Part No.	Nominal Diameter		Wall thickness s <sub>3</sub>	Width B	Shaft-Ø D <sub>J</sub> [h6, f7, h8]	Housing-Ø D <sub>H</sub> [H6, H7]	Bush-Ø D <sub>i,a</sub> Ass. in H6/H7 housing	Clearance C <sub>D</sub>					
	D <sub>i</sub>	D <sub>O</sub>							max. min.	max. min.	max. min.	max. min.	max. min.
0203DU	2	3.5	0.750 0.730	3.25	h6	H6	2.000 1.994	3.508 3.500	2.048 2.000				
0205DU				5.25						0.054 0.000			
0303DU	3	4.5		3.25							3.000 2.994	4.508 4.500	3.048 3.000
0305DU				2.75									
0306DU				4.75									
0403DU	4	5.5		3.25							h6	H6	4.000 3.992
0404DU				2.75									
0406DU				4.25									
0410DU				3.75									
0505DU	5	7		5.25	f7	H7	4.990 4.978	7.015 7.000	5.055 4.990				
0508DU				4.75									
0510DU				7.75									
0604DU	6	8	4.25	f7	H7	5.990 5.978	8.015 8.000	6.055 5.990					
0606DU			3.75										
0608DU			6.25										
0610DU			5.75										
0705DU	7	9	5.25	f7	H7	6.987 6.972	9.015 9.000	7.055 6.990					
0710DU			4.75						0.083 0.003				
				10.25									
				9.75									

## 8 Standard Products

Part No.	Nominal Diameter		Wall thickness $s_3$	Width B	Shaft- $\varnothing$ $D_J$ [h6, f7, h8]	Housing- $\varnothing$ $D_H$ [H6, H7]	Bush- $\varnothing$ $D_{i,a}$ Ass. in H6/H7 housing	Clearance $C_D$	
	$D_i$	$D_o$							max. min.
0806DU	8	10	1.005 0.980	6.25	7.987 7.972	10.015 10.000	8.055 7.990	0.083 0.003	
0808DU				5.75					
0810DU				8.25					
0812DU				7.75					
1006DU				10.25					
1008DU	9.75	9.987 9.972		12.018 12.000	10.058 9.990	0.086 0.003			
1010DU	12.25								
1012DU	11.75								
1015DU	15.25								
1020DU	14.75								
1208DU	12	14		8.25	11.984 11.966	14.018 14.000	12.058 11.990		0.092 0.006
1210DU				7.75					
1212DU				10.25					
1215DU				9.75					
1220DU				12.25					
1225DU	11.75	12.984 12.966		15.018 15.000	13.058 12.990	0.092 0.006			
1310DU	15.25								
1320DU	14.75								
1405DU	20.25								
1410DU	19.75								
1412DU	25.25	13.984 13.966	16.018 16.000	14.058 13.990	0.092 0.006				
1415DU	24.75								
1420DU	10.25								
1425DU	9.75								
1510DU	12.25					14.984 14.966	17.018 17.000	15.058 14.990	
1512DU	11.75								
1515DU	15.25								
1520DU	14.75								
1525DU	20.25								
1610DU	16	18	10.25	15.984 15.966	18.018 18.000	16.058 15.990	0.095 0.006		
1612DU			9.75						
1615DU			12.25						
1620DU			11.75						
1625DU			15.25						
1720DU	14.75	16.984 16.966	19.021 19.000	17.061 16.990	0.095 0.006				
1725DU	20.25								
1720DU	19.75								

Part No.	Nominal Diameter		Wall thickness $s_3$	Width B	Shaft- $\varnothing$ $D_J$ [h6, f7, h8]	Housing- $\varnothing$ $D_H$ [H6, H7]	Bush- $\varnothing D_{I,a}$ Ass. in H6/H7 housing	Clearance $C_D$
	$D_i$	$D_o$	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.
1810DU	18	20	1.005 0.980	10.25	17.984 17.966	20.021 20.000	18.061 17.990	0.095 0.006
1815DU				9.75				
1820DU				15.25				
1825DU				14.75				
2010DU				20.25				
2015DU	19.75	19.980 19.959	23.021 23.000	20.071 19.990	0.112 0.010			
2020DU	25.25							
2025DU	24.75							
2030DU	30.25							
2030DU	29.75							
2215DU	22	25	1.505 1.475	15.25	21.980 21.959	25.021 25.000	22.071 21.990	0.112 0.010
2220DU				14.75				
2225DU				20.25				
2230DU				19.75				
2230DU				25.25				
2415DU	24	27	1.505 1.475	15.25	23.980 23.959	27.021 27.000	24.071 23.990	0.112 0.010
2420DU				14.75				
2425DU				20.25				
2430DU				19.75				
2430DU				25.25				
2515DU	25	28	1.505 1.475	15.25	24.980 24.959	28.021 28.000	25.071 24.990	0.112 0.010
2520DU				14.75				
2525DU				20.25				
2530DU				19.75				
2550DU				25.25				
2815DU	28	32	1.505 1.475	15.25	27.980 27.959	32.025 32.000	28.085 27.990	0.112 0.010
2820DU				14.75				
2825DU				20.25				
2830DU				19.75				
2830DU				25.25				
3010DU	30	34	2.005 1.970	10.25	29.980 29.959	34.025 34.000	30.085 29.990	0.126 0.010
3015DU				9.75				
3020DU				15.25				
3025DU				14.75				
3030DU				20.25				
3040DU	19.75	31.975 31.950	36.025 36.000	32.085 31.990	0.135 0.015			
3220DU	30.25							
3230DU	29.75							
3240DU	40.25							
3240DU	39.75							

## 8 Standard Products


Part No.	Nominal Diameter		Wall thickness $s_3$	Width B	Shaft- $\varnothing$ $D_J$ [h6, f7, h8]	Housing- $\varnothing$ $D_H$ [H6, H7]	Bush- $\varnothing D_{i,a}$ Ass. in H6/H7 housing	Clearance $C_D$
	$D_i$	$D_o$						
3520DU	35	39	2.005 1.970	20.25	34.975 34.950	39.025 39.000	35.085 34.990	0.135 0.015
3530DU				19.75				
3535DU				30.25				
3540DU				29.75				
3550DU				35.25 34.75				
3720DU				37				
4020DU	40	44		20.25 19.75	39.975 39.950	44.025 44.000	40.085 39.990	
4030DU				30.25				
4040DU				29.75				
4050DU				40.25 39.75				
4520DU				45				
4530DU	30.25 29.75							
4540DU	40.25 39.75							
4545DU	45.25 44.75							
4550DU	50.25 49.75							
5020DU	50	55	20.25 19.75		49.975 49.950	55.030 55.000	50.110 49.990	
5030DU			30.25 29.75					
5040DU			40.25 39.75					
5050DU			50.25 49.75					
5060DU			60.25 59.75					
5520DU			55	60				20.25 19.75
5525DU	25.25 24.75							
5530DU	30.25 29.75							
5540DU	40.25 39.75							
5550DU	50.25 49.75							
5555DU	55.25 54.75							
5560DU	60.25 59.75							
6020DU	60	65			20.25 19.75	59.970 59.940	65.030 65.000	60.110 59.990
6030DU			30.25 29.75					
6040DU			40.25 39.75					
6050DU			50.25 49.75					
6060DU			60.25 59.75					
6070DU			70.25 69.75					

Part No.	Nominal Diameter		Wall thickness $s_3$	Width B	Shaft- $\varnothing$ $D_J$ [h6, f7, h8]	Housing- $\varnothing$ $D_H$ [H6, H7]	Bush- $\varnothing$ $D_{I,a}$ Ass. in H6/H7 housing	Clearance $C_D$					
	$D_i$	$D_o$							max. min.	max. min.	max. min.	max. min.	max. min.
6530DU	65	70	2.505 2.460	30.25	f7	H7	65.110 64.990	0.170 0.020					
6550DU				29.75					64.970	70.030			
6570DU				50.25					64.940	70.000			
7040DU	70	75		70.25					69.970	75.030	70.110	69.990	
7050DU				69.75									75.000
7070DU				40.25									74.970
7560DU	75	80		39.75					74.940	80.030	75.110	74.990	
7580DU				50.25									80.000
8040DU				49.75									80.030
8060DU	80	85		70.25					80.000	85.035	80.155	80.020	
8080DU				69.75									85.000
80100DU				60.25									85.035
8530DU	85	90	59.75	85.000	90.035	85.155	85.020						
8560DU			80.25					90.000					
85100DU			79.75					90.000					
9060DU	90	95	100.50	90.000	95.035	90.155	90.020						
90100DU			99.50					95.000					
9560DU			30.50					95.000	95.000				
95100DU	95	100	29.50	95.000	100.035	95.155	95.020						
10050DU			60.50					100.000					
10060DU			59.50					100.000					
10560DU	105	110	100.50	100.000	105.035	100.155	100.020						
105115DU			99.50					105.000					
11060DU			60.50					105.000	105.000				
110115DU	110	115	59.50	105.000	110.035	105.155	105.020						
11550DU			115.50					110.000					
11570DU			114.50					110.000					
12050DU	115	120	60.50	110.000	115.035	110.155	110.020						
12060DU			59.50					115.000					
125100DU			50.50					115.000	115.000				
13060DU	120	125	49.50	115.000	120.035	115.155	115.020						
12050DU			70.50					120.035	115.000				
12060DU			69.50					120.000					
125100DU	125	130	50.50	120.000	125.040	120.210	120.070						
13060DU			49.50					125.000					
130100DU			60.50					125.000	125.000				
13060DU	130	135	59.50	125.000	130.040	125.210	125.070						
130100DU			100.50					130.000					
13060DU			99.50					130.000					
130100DU	130	135	2.465 2.415	h8	H7	130.210 130.070	0.273 0.070						
12050DU			60.50					120.000	125.040				
12060DU			59.50					119.946	125.000				
120100DU	120	125	100.50	125.000	130.040	125.210	125.070						
125100DU			99.50					124.937	130.000				
13060DU			60.50					130.000	135.040				
130100DU	130	135	59.50	130.000	135.040	130.210	130.070						
13060DU			100.50					129.937	135.000				
130100DU			99.50					129.937					

## 8 Standard Products

Part No.	Nominal Diameter		Wall thickness $s_3$		Width B		Shaft- $\varnothing$ $D_J$ [h6, f7, h8]		Housing- $\varnothing$ $D_H$ [H6, H7]		Bush- $\varnothing$ $D_{i,a}$ Ass. in H6/H7 housing		Clearance $C_D$							
	$D_i$	$D_o$	max.	min.	max.	min.	max.	min.	max.	min.	max.	min.	max.	min.						
13560DU	135	140	2.465	2.415	h8	H7	135.000	134.937	140.040	140.000	135.210	135.070	0.273	0.070						
13580DU															60.50	59.50	80.50	79.50		
14060DU															140	145	60.50	59.50	140.000	139.937
140100DU	100.50	99.50																		
15060DU	150	155					60.50	59.50	150.000	149.937	155.040	155.000			150.210	150.070				
15080DU							80.50	79.50												
150100DU							100.50	99.50												
16080DU	160	165					80.50	79.50	160.000	159.937	165.040	165.000			160.210	160.070				
160100DU							100.50	99.50												
180100DU							180	185									180.000	179.937	185.046	185.000
200100DU	200	205					200.000	199.928	205.046	205.000	200.216	200.070								
210100DU	210	215					210.000	209.928	215.046	215.000	210.216	210.070								
220100DU	220	225					100.50	99.50	220.000	219.928	225.046	225.000			220.216	220.070				
250100DU	250	255							250.000	249.928	255.052	255.000			250.222	250.070				
300100DU	300	305							300.000	299.919	305.052	305.000			300.222	300.070				

### 8.2 DU Flanged Bushes

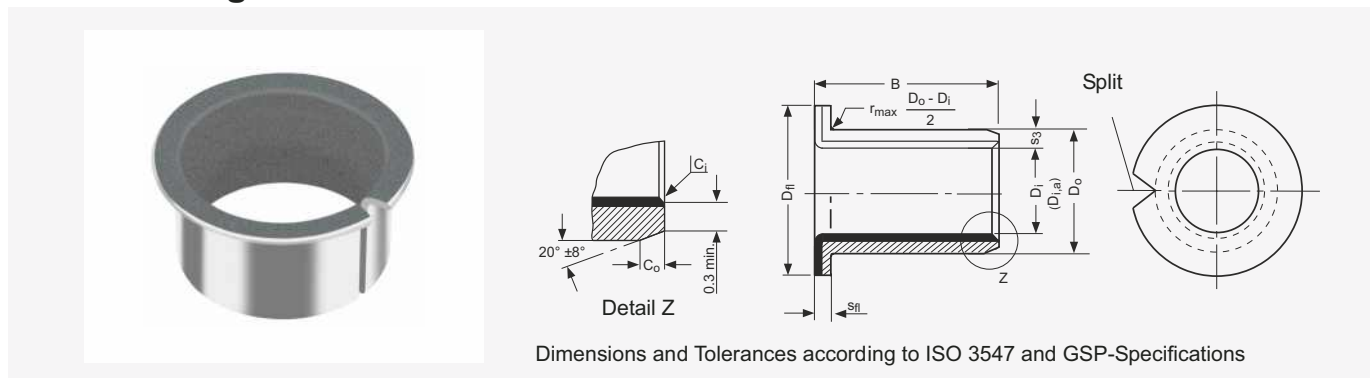

All dimensions in mm

#### Outside $C_o$ and Inside $C_i$ chamfers

Wall thickness $s_3$	$C_o$ (a)		$C_i$ (b)
	machined	rolled	
0.75	$0.5 \pm 0.3$	$0.5 \pm 0.3$	-0.1 to -0.4
1	$0.6 \pm 0.4$	$0.6 \pm 0.4$	-0.1 to -0.5
1.5	$0.6 \pm 0.4$	$0.6 \pm 0.4$	-0.1 to -0.7

Wall thickness $s_3$	$C_o$ (a)		$C_i$ (b)
	machined	rolled	
2	$1.2 \pm 0.4$	$1.0 \pm 0.4$	-0.1 to -0.7
2.5	$1.8 \pm 0.6$	$1.2 \pm 0.4$	-0.2 to -1.0


a = Chamfer  $C_o$  machined or rolled at the opinion of the manufacturer

b =  $C_i$  can be a radius or a chamfer in accordance with ISO 13715

Part No.	Nominal Diameter		Wall thickness $s_3$		Flange thickness $s_f$		Flange- $\varnothing$ $D_f$		Width B		Shaft- $\varnothing$ $D_J$ [h6, f7]		Housing- $\varnothing$ $D_H$ [H6, H7]		Bush- $\varnothing$ $D_{i,a}$ Ass. in H6/H7 housing		Clearance $C_D$			
	$D_i$	$D_o$	max.	min.	max.	min.	max.	min.	max.	min.	max.	min.	max.	min.	max.	min.	max.	min.		
BB0304DU	3	4.5	0.750	0.730	0.80	0.70	7.50	6.50	4.25	3.75	h6	3.000	2.994	H6	4.508	4.500	3.048	3.000	0.054	0.000
BB0404DU							4	5.5				9.50	8.50		4.000	3.992	5.508	4.500	4.048	4.000
BB0505DU	5	7	1.005	0.980	1.05	0.80	10.50	9.50	5.25	4.75	f7	4.990	4.978	H7	7.015	7.000	5.055	4.990	0.077	0.000

Part No.	Nominal Diameter		Wall thickness $S_3$	Flange thickness $S_{fl}$	Flange- $\varnothing$ $D_{fl}$	Width B	Shaft- $\varnothing$ $D_J$ [h6, f7]		Housing- $\varnothing$ $D_H$ [H6, H7]	Bush- $\varnothing$ $D_{i,a}$ Ass. in H6/H7 housing	Clearance $C_D$						
	$D_i$	$D_o$	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.						
BB0604DU	6	8	1.005 0.980	1.05 0.80	12.50	4.25	f7	H7	8.015	6.055	0.077						
BB0608DU						3.75						5.990	8.000	5.990			
BB0806DU	8	10			15.50	8.25						7.987	7.972	10.015	8.055	7.990	0.083
BB0808DU						7.75											
BB0810DU					5.75												
BB1007DU					5.25												
BB1009DU	10	12			18.50	7.75						9.987	9.972	12.018	10.058	9.990	0.086
BB1012DU						7.25											
BB1017DU					9.75												
BB1207DU					9.25												
BB1209DU	12	14			20.50	6.75						11.984	11.966	14.018	12.058	11.990	0.092
BB1212DU						9.25											
BB1217DU					8.75												
BB1412DU					8.75												
BB1417DU	14	16			22.50	12.25						13.984	13.966	16.018	14.058	13.990	0.092
BB1509DU						11.75											
BB1512DU					17.25												
BB1517DU					16.75												
BB1612DU	16	18			23.50	9.25						14.984	14.966	17.018	15.058	14.990	0.095
BB1617DU						8.75											
BB1812DU			12.25														
BB1817DU			11.75														
BB1822DU	18	20	26.50	17.25	17.984	17.966	20.021	18.061	17.990	0.095							
BB2012DU				16.75													
BB2017DU			22.25														
BB2022DU			21.75														
BB2512DU	25	28	35.50	11.75	19.980	19.959	23.021	20.071	19.990	0.112							
BB2517DU				16.75													
BB2522DU			16.25														
BB3016DU			11.25														
BB3026DU	30	34	42.50	21.25	29.980	29.959	34.025	30.085	29.990	0.126							
BB3516DU				16.25													
BB3526DU			15.75														
BB4016DU			26.25														
BB4026DU	40	44	53.50	25.75	34.975	34.950	39.025	35.085	34.990	0.135							
BB4516DU				16.25													
BB4526DU			15.75														
BB4526DU			26.25														
BB4526DU	45	50	58.50	25.75	44.975	44.950	50.025	45.105	44.990	0.155							
BB4526DU				15.75													

### 8.3 DU Flanged Washers

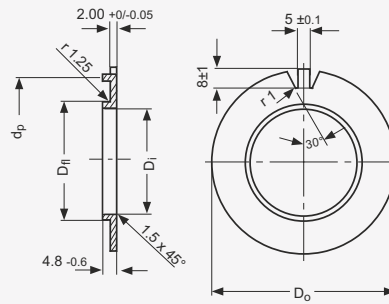

All dimensions in mm


Part No.	Inside-Ø D <sub>i</sub>	Outside-Ø D <sub>o</sub>	Flange-Ø D <sub>f</sub>	Location-Ø d <sub>p</sub>
	max. min.	max. min.	max. min.	max. min.
BS40DU	40.7 40.2	75.0 74.5	44.000 43.900	65.0 64.5
BS50DU	51.5 51.0	85.0 84.5	55.000 54.880	75.0 74.5
BS60DU	61.5 61.0	95.0 94.5	65.000 64.880	85.0 84.5
BS70DU	71.5 71.0	110.0 109.5	75.000 74.880	100.0 99.5
BS80DU	81.5 81.0	120.0 119.5	85.000 84.860	110.0 109.5
BS90DU	91.5 91.0	130.0 129.5	95.000 94.860	120.0 119.5
BS100DU	101.5 101.0	140.0 139.5	105.000 104.860	130.0 129.5

Corrosion Protection: Washers will be supplied covered with a light coating of oil.

Tab (Lug) Form: Washers are supplied with this feature in an unformed state (Flat). This feature may be supplied in the formed state only when requested by the customer.




### 8.4 DU Thrust Washer

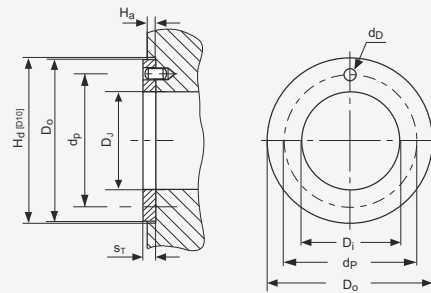

All dimensions in mm

Part No.	Inside-Ø D <sub>i</sub>		Outside-Ø D <sub>o</sub>		Thickness s <sub>T</sub> max. min.	Dowel Hole		Recess Depth H <sub>a</sub> max. min.
	min.	max.	max.	min.		Ø d <sub>D</sub> max. min.	PCD-Ø d <sub>P</sub> max. min.	
WC08DU	10.00	10.25	20.00	19.75	1.50 1.45	No Hole	No Hole	1.20 0.95
WC10DU	12.00	12.25	24.00	23.75		1.875 1.625	18.12 17.88	
WC12DU	14.00	14.25	26.00	25.75		2.375 2.125	20.12 19.88	
WC14DU	16.00	16.25	30.00	29.75			22.12 21.88	
WC16DU	18.00	18.25	32.00	31.75		3.375 3.125	25.12 24.88	
WC18DU	20.00	20.25	36.00	35.75			28.12 27.88	
WC20DU	22.00	22.25	38.00	37.75		4.375 4.125	30.12 29.88	
WC22DU	24.00	24.25	42.00	41.75			33.12 32.88	
WC24DU	26.00	26.25	44.00	43.75		61.12 60.88	35.12 34.88	
WC25DU	28.00	28.25	48.00	47.75			38.12 37.88	
WC30DU	32.00	32.25	54.00	53.75		65.12 64.88	43.12 42.88	
WC35DU	38.00	38.25	62.00	61.75			50.12 49.88	
WC40DU	42.00	42.25	66.00	65.75		76.12 75.88	54.12 53.88	
WC45DU	48.00	48.25	74.00	73.75			61.12 60.88	
WC50DU	52.00	52.25	78.00	77.75	2.00 1.95	65.12 64.88	1.70 1.45	
WC60DU	62.00	62.25	90.00	89.75		76.12 75.88		

## 8.5 DU-B Cylindrical Bushes

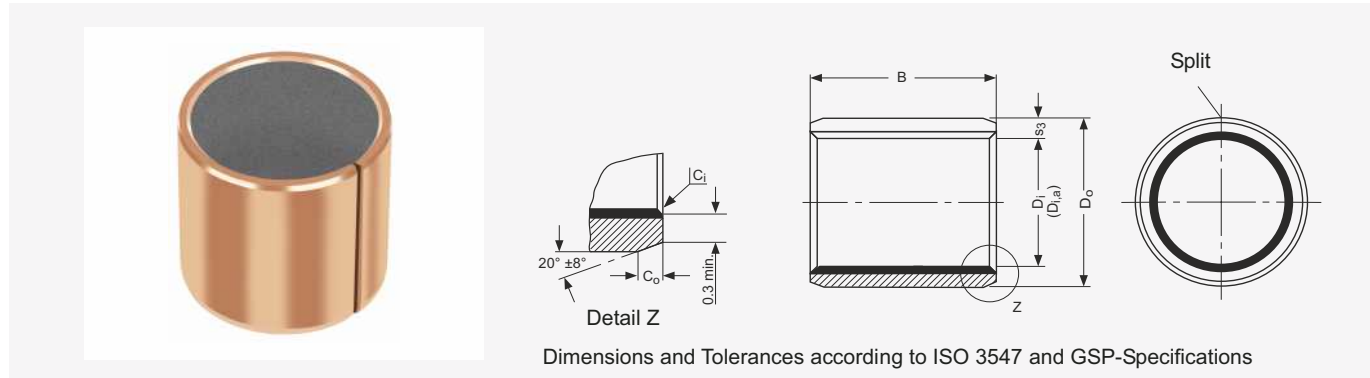

All dimensions in mm

### Outside Co and Inside Ci chamfers

Wall thickness s <sub>3</sub>	C <sub>0</sub> (a)		C <sub>i</sub> (b)
	machined	rolled	
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7

Wall thickness s <sub>3</sub>	C <sub>0</sub> (a)		C <sub>i</sub> (b)
	machined	rolled	
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

a = Chamfer C<sub>0</sub> machined or rolled at the opinion of the manufacturer

b = C<sub>i</sub> can be a radius or a chamfer in accordance with ISO 13715


Part No.	Nominal Diameter		Wall thickness s <sub>3</sub>	Width B	Shaft-Ø D <sub>J</sub> [h6, f7, h8]		Housing-Ø D <sub>H</sub> [H6, H7]		Bush-Ø D <sub>i,a</sub> ass. in H6/H7 housing	Clearance C <sub>D</sub>
	D <sub>i</sub>	D <sub>o</sub>			max. min.	max. min.	max. min.	max. min.		
0203DUB	2	3.5	0.750 0.730	3.25	h6	2.000 1.994	H6	3.508 3.500	2.048 2.000	0.054 0.000
0205DUB				5.25 4.75						
0306DUB	3	4.5	0.750 0.730	6.25 5.75	h6	3.000 2.994	H6	4.508 4.500	3.048 3.000	0.056 0.000
0404DUB				4.25 3.75						
0406DUB	4	5.5	0.750 0.730	6.25 5.75	h6	4.000 3.992	H6	5.508 5.500	4.048 4.000	0.077 0.000
0505DUB				5.25 4.75						
0510DUB	5	7	0.750 0.730	10.25 9.75	h6	4.990 4.978	H6	7.015 7.000	5.055 4.990	0.083 0.003
0606DUB				6.25 5.75						
0608DUB	6	8	0.750 0.730	8.25 7.75	h6	5.990 5.978	H6	8.015 8.000	6.055 5.990	0.086 0.003
0610DUB				10.25 9.75						
0808DUB	8	10	1.005 0.980	8.25 7.75	f7	7.987 7.972	H7	10.015 10.000	8.055 7.990	0.086 0.003
0810DUB				10.25 9.75						
0812DUB	8	10	1.005 0.980	12.25 11.75	f7	9.987 9.972	H7	12.018 12.000	10.058 9.990	0.092 0.006
1010DUB				10.25 9.75						
1015DUB	10	12	1.005 0.980	15.25 14.75	f7	11.984 11.966	H7	14.018 14.000	12.058 11.990	0.092 0.006
1208DUB				8.25 7.75						
1210DUB	12	14	1.005 0.980	10.25 9.75	f7	11.984 11.966	H7	14.018 14.000	12.058 11.990	0.092 0.006
1212DUB				12.25 11.75						
1215DUB	12	14	1.005 0.980	15.25 14.75	f7	11.984 11.966	H7	14.018 14.000	12.058 11.990	0.092 0.006
				12.25 11.75						

Part No.	Nominal Diameter		Wall thickness $s_3$	Width B	Shaft- $\varnothing$ $D_J$ [h6, f7, h8]	Housing- $\varnothing$ $D_H$ [H6, H7]	Bush- $\varnothing$ $D_{I,a}$ ass. in H6/H7 housing	Clearance $C_D$
	$D_i$	$D_o$						
1410DUB	14	16	1.005 0.980	10.25	13.984 13.966	16.018 16.000	14.058 13.990	0.092 0.006
1415DUB				9.75				
1420DUB				15.25				
1515DUB	15	17		14.75	14.984 14.966	17.018 17.000	15.058 14.990	
1525DUB				20.25				
1615DUB				19.75				
1625DUB	16	18		15.25	15.984 15.966	18.018 18.000	16.058 15.990	
1820DUB				14.75				
1825DUB				25.25				
2015DUB	20	23		24.75	19.980 19.959	23.021 23.000	20.071 19.990	
2020DUB				20.25				
2025DUB				19.75				
2030DUB				25.25				
2215DUB	22	25		24.75	21.980 21.959	25.021 25.000	22.071 21.990	
2220DUB				15.25				
2225DUB			14.75					
2515DUB			20.25					
2525DUB	25	28	19.75	24.980 24.959	28.021 28.000	25.071 24.990		
2830DUB			25.25					
3020DUB			24.75					
3030DUB	30	34	30.25	29.980 29.959	34.025 34.000	30.085 29.990		
3040DUB			29.75					
3520DUB			40.25					
3530DUB	35	39	39.75	34.975 34.950	39.025 39.000	35.085 34.990		
4030DUB			20.25					
4050DUB			19.75					
4530DUB	45	50	30.25	44.975 44.950	50.025 50.000	45.105 44.990		
4550DUB			29.75					
5040DUB			50.25					
5060DUB	50	55	49.75	49.975 49.950	55.030 55.000	50.110 49.990		
5540DUB			60.25					
6040DUB			59.75					
6050DUB	60	65	59.75	59.970 59.940	65.030 65.000	60.110 59.990		
6060DUB			40.25					
6070DUB			39.75					
6570DUB			50.25					
6570DUB	65	70	49.75	64.970 64.940	70.030 70.000	65.110 64.990		
6570DUB			69.75					

## 8 Standard Products

Part No.	Nominal Diameter		Wall thickness $s_3$	Width B	Shaft- $\varnothing$ $D_J$ [h6, f7, h8]	Housing- $\varnothing$ $D_H$ [H6, H7]	Bush- $\varnothing$ $D_{i,a}$ ass. in H6/H7 housing	Clearance $C_D$
	$D_i$	$D_o$						
7050DUB	70	75	2.505 2.460	50.25	f7	69.970 69.940	75.030 75.000	70.110 69.990
7070DUB				49.75				
7580DUB	75	80	2.490 2.440	80.25	h7	74.970 74.940	80.030 80.000	75.110 74.990
8060DUB	80	85		79.75				
80100DUB			85	90	100.50 99.50	h8	85.000 84.946	90.035 90.000
85100DUB	60.50 59.50	90.000 89.946			H7			
9060DUB	90	95	2.490 2.440	100.50 99.50	h8	95.000 94.946	100.035 100.000	95.155 95.020
90100DUB				60.50 59.50				
95100DUB	95	100	2.490 2.440	100.50 99.50	h8	95.000 94.946	100.035 100.000	95.155 95.020
10060DUB				60.50 59.50				
100115DUB	100	105	2.490 2.440	115.50 114.50	h8	100.000 99.946	105.035 105.000	100.155 100.020
105115DUB				60.50 59.50				
105115DUB	105	110	2.490 2.440	115.50 114.50	h8	105.000 104.946	110.035 110.000	105.155 105.020
110115DUB				60.50 59.50				
110115DUB	110	115	2.490 2.440	115.50 114.50	h8	110.000 109.946	115.035 115.000	115.155 115.020

### 8.6 DU-B Flanged Bushes

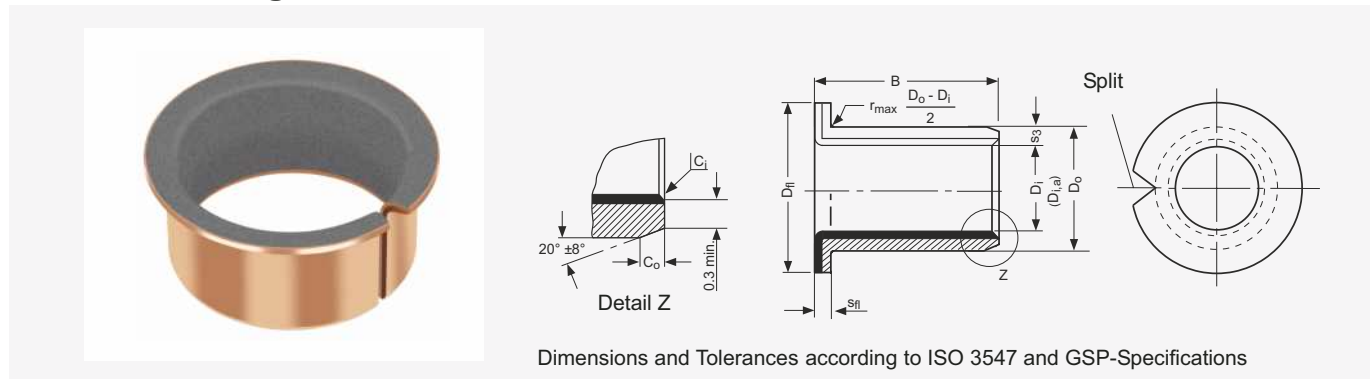

All dimensions in mm

#### Outside $C_0$ and Inside $C_1$ chamfers

Wall thickness $s_3$	$C_0$ (a)		$C_1$ (b)
	machined	rolled	
0.75	$0.5 \pm 0.3$	$0.5 \pm 0.3$	-0.1 to -0.4
1	$0.6 \pm 0.4$	$0.6 \pm 0.4$	-0.1 to -0.5
1.5	$0.6 \pm 0.4$	$0.6 \pm 0.4$	-0.1 to -0.7

Wall thickness $s_3$	$C_0$ (a)		$C_1$ (b)
	machined	rolled	
2	$1.2 \pm 0.4$	$1.0 \pm 0.4$	-0.1 to -0.7
2.5	$1.8 \pm 0.6$	$1.2 \pm 0.4$	-0.2 to -1.0

a = Chamfer  $C_0$  machined or rolled at the opinion of the manufacturer


b =  $C_1$  can be a radius or a chamfer in accordance with ISO 13715

Part No.	Nominal Diameter		Wall thickness $s_3$	Flange thickness $s_{fl}$	Flange- $\varnothing$ $D_{fl}$	Width B	Shaft- $\varnothing$ $D_J$ [h6, f7, h8]	Housing- $\varnothing$ $D_H$ [H6, H7]	Bush- $\varnothing$ $D_{i,a}$ Ass. in H6/H7 housing	Clearance $C_D$
	$D_i$	$D_o$								
BB0304DUB	3	4.5	0.750 0.730	0.80 0.70	7.50	4.25	h6	H6	4.508 4.500	3.048 3.000
BB0404DUB					6.50					
BB0505DUB	5	7	1.005 0.980	1.05 0.80	10.50	5.25 4.75	f7	H7	7.015	5.055
					9.50				4.978	7.000

Part No.	Nominal Diameter		Wall thickness $S_3$	Flange thickness $S_{fl}$	Flange- $\varnothing$ $D_{fl}$	Width B	Shaft- $\varnothing$ $D_J$ [h6, f7, h8]	Housing- $\varnothing$ $D_H$ [H6, H7]	Bush- $\varnothing$ $D_{i,a}$ Ass. in H6/H7 housing	Clearance $C_D$	
	$D_i$	$D_o$	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	
BB0604DUB	6	8	1.005 0.980	1.05 0.80	12.50 11.50	4.25	f7	5.990 5.978	8.015 8.000	6.055 5.990	0.077 0.000
BB0608DUB						3.75					
BB0806DUB	8	10			15.50 14.50	8.25		7.987 7.972	10.015 10.000	8.055 7.990	0.083 0.000
BB0810DUB						7.75					
BB1007DUB	10	12			18.50 17.50	5.75		9.987 9.972	12.018 12.000	10.058 9.990	0.086 0.003
BB1012DUB						5.25					
BB1207DUB	12	14			20.50 19.50	9.25		11.984 11.966	14.018 14.000	12.058 11.990	0.092 0.006
BB1209DUB						7.25					
BB1212DUB						6.75					
BB1417DUB	14	16			22.50 21.50	9.25		13.984 13.966	16.018 16.000	14.058 13.990	0.092 0.006
BB1512DUB						6.75					
BB1517DUB	15	17			23.50 22.50	8.75		14.984 14.966	17.018 17.000	15.058 14.990	0.092 0.006
BB1612DUB						12.25					
BB1617DUB	16	18			24.50 23.50	11.75		15.984 15.966	18.018 18.000	16.058 15.990	0.092 0.006
BB1812DUB						12.25					
BB1822DUB	18	20			26.50 25.50	11.75		17.984 17.966	20.021 20.000	18.061 17.990	0.095 0.006
BB2012DUB			22.25								
BB2017DUB	20	23	30.50 29.50	21.75	19.980 19.959	23.021 23.000	20.071 19.990	0.112 0.010			
BB2512DUB				11.75							
BB2522DUB	25	28	35.50 34.50	11.25	24.980 24.959	28.021 28.000	25.071 24.990	0.126 0.010			
BB3016DUB				21.25							
BB3026DUB	30	34	42.50 41.50	16.25	29.980 29.959	34.025 34.000	30.085 29.990	0.135 0.015			
BB3526DUB				15.75							
BB4026DUB	35	39	47.50 46.50	26.25	34.975 34.950	39.025 39.000	35.085 34.990	0.135 0.015			
BB4526DUB				25.75							
BB4526DUB	45	50	58.50 57.50	26.25	44.975 44.950	50.025 50.000	45.105 44.990	0.155 0.015			
BB4526DUB				25.75							

# 8 Standard Products

## 8.7 DU Cylindrical Bushes - Inch sizes

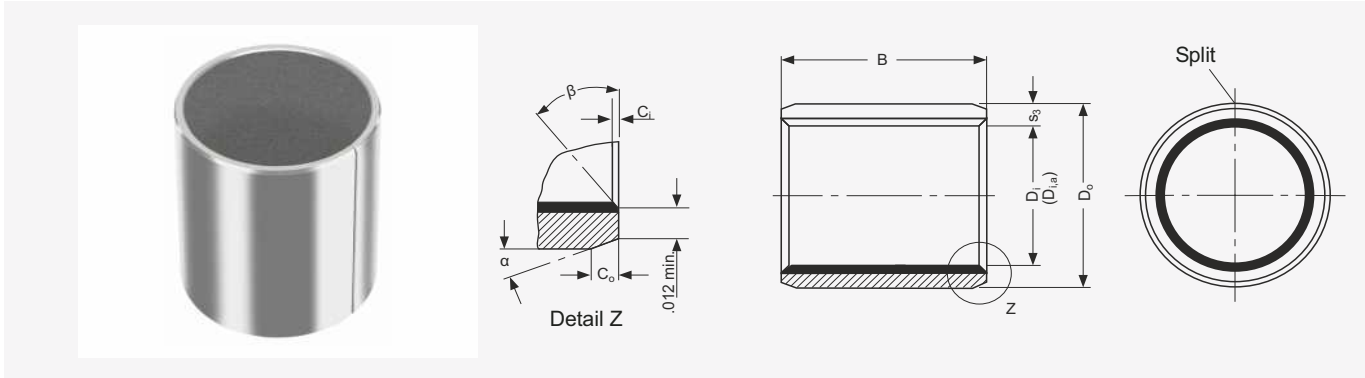

All dimensions in inch

### ID and OD chamfers

$D_i$	$C_o$	$\alpha$	$C_i$	$\beta$
1/8" - 5/16"	0.008" - 0.024"	30°-45°	0.004" - 0.012"	30°-45°
3/8" - 11/16"	0.020" - 0.040"	20°-30°	0.005" - 0.025"	40°-55°
3/4" - 7"	0.020" - 0.040"	15°-25°	0.005" - 0.025"	40°-50°

Part No.	Nominal Diameter			Wall thickness $s_3$	Width B	Shaft- $\varnothing$ $D_j$	Housing- $\varnothing$ $D_H$	Bush- $\varnothing$ $D_{i,a}$ Ass. in $D_H$ housing	Clearance $C_D$																																																																																																					
	$D_i$	$D_o$	B							max. min.	max. min.	max. min.	max. min.	max. min.																																																																																																
02DU02	1/8	3/16	1/8	0.0315 0.0305	0.1350 0.1150	0.1243 0.1236	0.1878 0.1873	0.1268 0.1243	0.0032 0.0000																																																																																																					
02DU03			3/16		0.1975 0.1775					025DU025	5/32	7/32	5/32	0.16625 0.14265	0.1554 0.1547	0.2191 0.2186	0.1581 0.1556	0.0034 0.0002	025DU04	1/4	0.2600 0.2400	03DU03	3/16	1/4	3/16	0.1975 0.1775	0.1865 0.1858	0.2503 0.2497	0.1893 0.1867	0.0035 0.0002	03DU04	1/4	0.2600 0.2400	03DU06	3/8	0.3850 0.3650	04DU04	1/4	5/16	1/4	0.2600 0.2400	0.2490 0.2481	0.3128 0.3122	0.2518 0.2492	0.0037 0.0002	04DU06	3/8	0.3850 0.3650	05DU06	5/16	3/8	3/8	0.3850 0.3650	0.3115 0.3106	0.3753 0.3747	0.3143 0.3117	05DU08	1/2	0.5100 0.4900	06DU06	3/8	15/32	3/8	0.3850 0.3650	0.3740 0.3731	0.4691 0.4684	0.3769 0.3742	0.0038 0.0002	06DU08	1/2	0.5100 0.4900	06DU12	3/4	0.7600 0.7400	07DU08	7/16	17/32	1/2	0.5100 0.4900	0.4365 0.4355	0.5316 0.5309	0.4394 0.4367	0.0039 0.0002	07DU12	3/4	0.7600 0.7400	08DU06	1/2	19/32	3/8	0.3850 0.3650	0.4990 0.4980	0.5941 0.5934	0.5019 0.4992	0.0039 0.0002	08DU08	1/2	0.5100 0.4900	08DU10	5/8	0.6350 0.6150	08DU14	7/8	0.8850 0.8650	09DU08	9/16	21/32	1/2	0.5100 0.4900	0.5615 0.5605
025DU025	5/32	7/32	5/32		0.16625 0.14265	0.1554 0.1547	0.2191 0.2186	0.1581 0.1556	0.0034 0.0002																																																																																																					
025DU04			1/4		0.2600 0.2400					03DU03	3/16	1/4	3/16	0.1975 0.1775	0.1865 0.1858	0.2503 0.2497	0.1893 0.1867	0.0035 0.0002	03DU04	1/4	0.2600 0.2400	03DU06			3/8	0.3850 0.3650					04DU04	1/4	5/16	1/4	0.2600 0.2400	0.2490 0.2481	0.3128 0.3122	0.2518 0.2492	0.0037 0.0002	04DU06	3/8	0.3850 0.3650	05DU06	5/16		3/8	3/8	0.3850 0.3650	0.3115 0.3106	0.3753 0.3747	0.3143 0.3117	05DU08	1/2	0.5100 0.4900	06DU06	3/8	15/32	3/8	0.3850 0.3650	0.3740 0.3731			0.4691 0.4684	0.3769 0.3742					0.0038 0.0002	06DU08	1/2	0.5100 0.4900	06DU12	3/4	0.7600 0.7400	07DU08	7/16	17/32	1/2	0.5100 0.4900	0.4365 0.4355	0.5316 0.5309	0.4394 0.4367	0.0039 0.0002	07DU12	3/4	0.7600 0.7400			08DU06	1/2					19/32	3/8	0.3850 0.3650	0.4990 0.4980	0.5941 0.5934	0.5019 0.4992	0.0039 0.0002	08DU08	1/2	0.5100 0.4900	08DU10	5/8	0.6350 0.6150	08DU14	7/8
03DU03	3/16	1/4	3/16		0.1975 0.1775	0.1865 0.1858	0.2503 0.2497	0.1893 0.1867	0.0035 0.0002																																																																																																					
03DU04			1/4		0.2600 0.2400																																																																																																									
03DU06			3/8		0.3850 0.3650																																																																																																									
04DU04	1/4	5/16	1/4		0.2600 0.2400	0.2490 0.2481	0.3128 0.3122	0.2518 0.2492	0.0037 0.0002																																																																																																					
04DU06			3/8		0.3850 0.3650																																																																																																									
05DU06	5/16	3/8	3/8		0.3850 0.3650	0.3115 0.3106	0.3753 0.3747	0.3143 0.3117																																																																																																						
05DU08			1/2		0.5100 0.4900																																																																																																									
06DU06	3/8	15/32	3/8		0.3850 0.3650	0.3740 0.3731	0.4691 0.4684	0.3769 0.3742	0.0038 0.0002																																																																																																					
06DU08			1/2		0.5100 0.4900																																																																																																									
06DU12			3/4		0.7600 0.7400																																																																																																									
07DU08	7/16	17/32	1/2		0.5100 0.4900	0.4365 0.4355	0.5316 0.5309	0.4394 0.4367	0.0039 0.0002																																																																																																					
07DU12			3/4		0.7600 0.7400																																																																																																									
08DU06	1/2	19/32	3/8	0.3850 0.3650	0.4990 0.4980	0.5941 0.5934	0.5019 0.4992	0.0039 0.0002																																																																																																						
08DU08			1/2	0.5100 0.4900																																																																																																										
08DU10			5/8	0.6350 0.6150																																																																																																										
08DU14			7/8	0.8850 0.8650																																																																																																										
09DU08	9/16	21/32	1/2	0.5100 0.4900	0.5615 0.5605	0.6566 0.6559	0.5644 0.5617																																																																																																							
09DU12			3/4	0.7600 0.7400																																																																																																										


Part No.	Nominal Diameter			Wall thickness $s_3$	Width B	Shaft- $\varnothing$ $D_J$	Housing- $\varnothing$ $D_H$	Bush- $\varnothing$ $D_{1,a}$ Ass. in $D_H$ housing	Clearance $C_D$
	$D_i$	$D_o$	B						
10DU08	5/8	23/32	1/2	0.0471 0.0461	0.5100 0.4900	0.6240 0.6230	0.7192 0.7184	0.6270 0.6242	0.0040 0.0002
10DU10			5/8		0.6350 0.6150				
10DU12			3/4		0.7600 0.7400				
10DU14			7/8		0.8850 0.8650				
11DU14	11/16	25/32	7/8		0.8850 0.8650	0.6865 0.6855	0.7817 0.7809	0.6895 0.6867	
12DU08	3/4	7/8	1/2	0.0627 0.0615	0.5100 0.4900	0.7491 0.7479	0.8755 0.8747	0.7525 0.7493	0.0046 0.0002
12DU12			3/4		0.7600 0.7400				
12DU16			1		1.0100 0.9900				
14DU12	7/8	1	3/4		0.7600 0.7400	0.8741 0.8729	1.0005 0.9997	0.8775 0.8743	0.0047 0.0001
14DU14			7/8	0.8850 0.8650					
14DU16			1	1.0100 0.9900					
16DU12	1	1 1/8	3/4		0.7600 0.7400	0.9991 0.9979	1.1256 1.1246	1.0026 0.9992	0.0052 0.0002
16DU16			1	1.0100 0.9900					
16DU24			1 1/2	1.5100 1.4900					
18DU12	1 1/8	1 9/32	3/4		0.7600 0.7400	1.1238 1.1226	1.2818 1.2808	1.1278 1.1240	0.0056 0.0002
18DU16			1	1.0100 0.9900					
20DU12	1 1/4	1 13/32	3/4		0.7600 0.7400	1.2488 1.2472	1.4068 1.4058	1.2528 1.2490	0.0056 0.0002
20DU16			1	1.0100 0.9900					
20DU20			1 1/4	1.2600 1.2400					
20DU28			1 3/4	1.7600 1.7400					
22DU16	1 3/8	1 17/32	1		1.0100 0.9900	1.3738 1.3722	1.5318 1.5308	1.3778 1.3740	0.0056 0.0002
22DU22			1 3/8	1.3850 1.3650					
22DU28			1 3/4	1.7600 1.7400					
24DU16	1 1/2	1 21/32	1		1.0100 0.9900	1.4988 1.4972	1.6568 1.6558	1.5028 1.4990	0.0056 0.0002
24DU20			1 1/4	1.2600 1.2400					
24DU24			1 1/2	1.5100 1.4900					
24DU32			2	2.0100 1.9900					
26DU16	1 5/8	1 25/32	1		1.0100 0.9900	1.6238 1.6222	1.7818 1.7808	1.6278 1.6240	0.0064 0.0002
26DU24			1 1/2	1.5100 1.4900					
28DU16	1 3/4	1 15/16	1		1.0100 0.9900	1.7487 1.7471	1.9381 1.9371	1.7535 1.7489	0.0064 0.0002
28DU24			1 1/2	1.5100 1.4900					
28DU28			1 3/4	1.7600 1.7400					
28DU32			2	2.0100 1.9900					

## 8 Standard Products

Part No.	Nominal Diameter			Wall thickness $S_3$	Width B	Shaft- $\varnothing$ $D_J$	Housing- $\varnothing$ $D_H$	Bush- $\varnothing$ $D_{I,a}$ Ass. in $D_H$ housing	Clearance $C_D$	
	$D_i$	$D_o$	B	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	
30DU16	$1\frac{7}{8}$	$2\frac{1}{16}$	1	0.0941 0.0923	1.0100 0.9900	1.8737 1.8721	2.0633 2.0621	1.8787 1.8739	0.0066 0.0002	
30DU30			$1\frac{7}{8}$		1.8850 1.8650					
30DU36			$2\frac{1}{4}$		2.2600 2.2400					
32DU16	2	$2\frac{3}{16}$	1		1.0100 0.9900	1.9987 1.9969	2.1883 2.1871	2.0037 1.9989		0.0068 0.0002
32DU24			$1\frac{1}{2}$		1.5100 1.4900					
32DU32			2		2.0100 1.9900					
32DU40			$2\frac{1}{2}$	2.5100 2.4900						
36DU32	$2\frac{1}{4}$	$2\frac{7}{16}$	2	0.0928 0.0902	2.0100 1.4900	2.2507 2.2489	2.4377 2.4365	2.2573 2.2509	0.0084 0.0002	
36DU36			$2\frac{1}{4}$		2.2600 2.2400					
36DU40			$2\frac{1}{2}$		2.5100 2.4900					
36DU48			3		3.0100 2.9900					
40DU32	$2\frac{1}{2}$	$2\frac{11}{16}$	2		2.0100 1.9900	2.5011 2.4993	2.6881 2.6869	2.5077 2.5013		0.0084 0.0002
40DU40			$2\frac{1}{2}$		2.5100 2.4900					
40DU48			3		3.0100 2.9900					
40DU56			$3\frac{1}{2}$		3.5100 3.4900					
44DU32	$2\frac{3}{4}$	$2\frac{15}{16}$	2		2.0100 1.9900	2.7500 2.7482	2.9370 2.9358	2.7566 2.7502		0.0086 0.0002
44DU40			$2\frac{1}{2}$		2.5100 2.4900					
44DU48			3		3.0100 2.9900					
44DU56			$3\frac{1}{2}$		3.5100 3.4900					
48DU32	3	$3\frac{3}{16}$	$2\frac{1}{2}$	2.5100 2.4900	3.0000 2.9982	3.1872 3.1858	3.0068 3.0002	0.0086 0.0002		
48DU48			3	3.0100 2.9900						
48DU60			$3\frac{3}{4}$	3.7600 3.7400						
56DU40	$3\frac{1}{2}$	$3\frac{11}{16}$	$2\frac{1}{2}$	2.5100 2.4900	3.5000 3.4978	3.6872 3.6858	3.5068 3.5002	0.0090 0.0002		
56DU48			3	3.0100 2.9900						
56DU60			$3\frac{3}{4}$	3.7600 3.7400						
64DU48	4	$4\frac{3}{16}$	3	3.0100 2.9900	4.0000 3.9978	4.1872 4.1858	4.0068 4.0002	0.0090 0.0002		
64DU60			$3\frac{3}{4}$	3.7600 3.7400						
64DU76			$4\frac{3}{4}$	4.7600 4.7400						
80DU48	5	$5\frac{3}{16}$	3	3.0100 2.9900	4.9986 4.9961	5.1860 5.1844	5.0056 4.9988	0.0095 0.0002		
80DU60			$3\frac{3}{4}$	3.7600 3.7400						
96DU48			3	3.0100 2.9900						
96DU60	6	$6\frac{3}{16}$	$3\frac{3}{4}$	3.7600 3.7400	6.0000 5.9975	6.1874 6.1858	6.0070 6.0002	0.0097 0.0002		
112DU60			7	$7\frac{3}{16}$					$3\frac{3}{4}$	3.7600 3.7400



### 8.8 DU Thrust Washers - Inch sizes

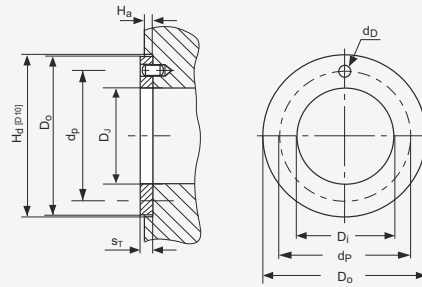


All dimensions in inch

Part No.	Inside-Ø D <sub>i</sub>		Outside-Ø D <sub>o</sub>		Thickness s <sub>T</sub> max. min.	Dowel Hole		Recess Depth H <sub>a</sub> max. min.	
	max.	min.	max.	min.		Ø d <sub>D</sub>	PCD-Ø d <sub>P</sub>		
						max. min.	max. min.		
DU06	0.510	0.500	0.875	0.865	0.063 0.061	0.077 0.067	0.692	0.050 0.040	
DU07	0.572	0.562	1.000	0.990			0.682		
DU08	0.635	0.625	1.125	1.115		0.109 0.099	0.786		
DU09	0.697	0.687	1.187	1.177			0.776		
DU10	0.760	0.750	1.250	1.240			0.880		
DU11	0.822	0.812	1.375	1.365		0.140 0.130	0.870		
DU12	0.885	0.875	1.500	1.490			0.942		
DU14	1.010	1.000	1.750	1.740		0.171 0.161	0.932		
DU16	1.135	1.125	2.000	1.990			1.005		
DU18	1.260	1.250	2.125	2.115			0.995		
DU20	1.385	1.375	2.250	2.240		0.202 0.192	1.099		
DU22	1.510	1.500	2.500	2.490			1.089		
DU24	1.635	1.625	2.625	2.615		0.093 0.091	1.192		0.080 0.070
DU26	1.760	1.750	2.750	2.740			1.182		
DU28	2.010	2.000	3.000	2.990	1.380				
DU30	2.135	2.125	3.125	3.115	1.370				
DU32	2.260	2.250	3.250	3.240		1.567			
						1.557			
						1.692			
						1.682			
						1.817			
						1.807			
						2.005			
						1.995			
						2.130			
						2.120			
						2.255			
						2.245			
						2.505			
						2.495			
						2.630			
						2.620			
						2.755			
						2.745			

## 8 Standard Products

### 8.9 DU Strip

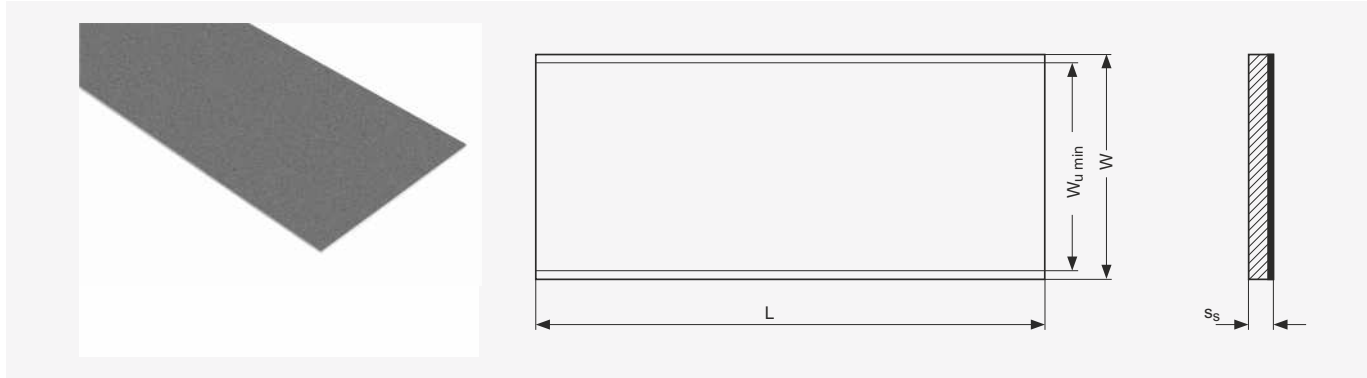

All dimensions in mm

Part No.	Length L		Total Width W	Usable Width $W_{U \min}$	Thickness $s_S$	
	max.	min.			max.	min.
S07190DU	503	500	200	190	0.74	0.70
S10190DU					1.01	0.97
S15240DU					1.52	1.48
S20240DU			254	240	2.00	1.96
S25240DU					2.50	2.46
S30240DU					3.06	3.02

### 8.10 DU-B Strip

All dimensions in mm

Part No.	Length L		Total Width W	Usable Width $W_{U \min}$	Thickness $s_S$	
	max.	min.			max.	min.
S07085DUB	503	500	95	85	0.74	0.70
S10180DUB					1.01	0.97
S15180DUB					1.52	1.48
S20180DUB			193	180	2.00	1.96
S25180DUB					2.50	2.46

### 8.11 DU Strip - Inch sizes

DU Strip Inch sizes are available as Non-Standard products, on request.

## 9 Test Methods

### 9.1 Measurement of Wrapped Bushes

It is not possible to accurately measure the external and internal diameters of a wrapped bush in the free condition. In its free state a wrapped bush will not be perfectly cylindrical and the butt joint may be open. When correctly installed in a housing the butt joint will be tightly closed and the bush will conform to the housing.

For this reason the external diameter and internal diameter of a wrapped bush can only be checked with special gauges and test equipment.

The checking methods are defined in ISO 3547 Parts 1 to 7.

#### Test A of ISO 3547 Part 2

Checking the external diameter in a test machine with checking blocks and adjusting mandrel.

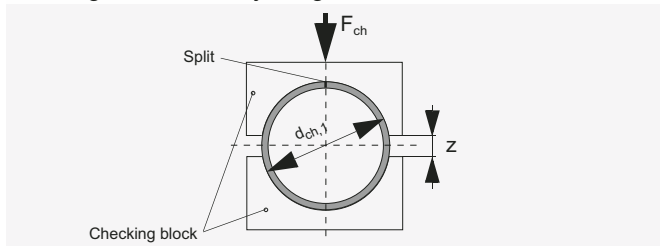


Fig. 34: Test A, Data for drawing

Test A of ISO 3547 Part 2 on 2015DU	
Checking block and setting mandrel $d_{ch,1}$	23.062 mm
Test force $F_{ch}$	4500 N
Limits for $\Delta z$	0 and -0.065 mm
Bush Outside diameter $D_o$	23.035 to 23.075 mm

Table 14: Test A of ISO 3547 Part 2

#### Test B (alternatively to Test A)

Check external diameter with GO and NOGO ring gauges.

#### Test C

Checking the internal diameter of a bush pressed into a ring gauge, which nominal diameter corresponds to the dimension specified in table 6 of ISO 3547 Part 2 (Example  $D_i = 20$  mm).

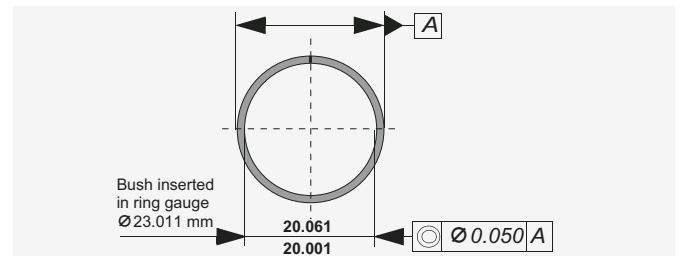


Fig. 35: Test C, Data for drawing

#### Measurement of Wall Thickness (alternatively to Test C)

The wall thickness is measured at one, two or three positions axially according to the bearing dimensions.

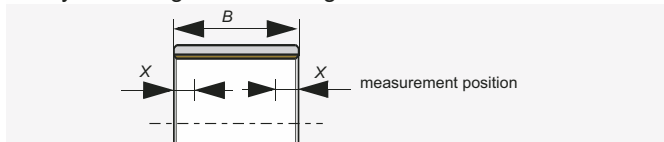


Fig. 36: Measurement position

B [mm]	X [mm]	measurement position
$\leq 15$	B/2	1
$> 15 \leq 50$	4	2
$> 50 \leq 90$	6 and B/2	3
$> 90$	8 and B/2	3

Table 15: Measurement position

#### Test D

Check external diameter by precision measuring tape.

## 9 Test Methods

---

Your notes:

## Formula Symbols and Designations

Formula Symbol	Unit	Designation
$A$	$\text{mm}^2$	Surface Area of DU bearing
$A_M$	$\text{mm}^2$	Surface Area of mating surface in contact with DU bearing (slideway)
$a_B$	-	Bearing size factor
$a_C$	-	Application factor for bore burnishing or machining
$a_E$	-	High load factor
$a_{E1}$	-	Specific load factor (slideways)
$a_{E2}$	-	Speed, temperature and material factor (slideways)
$a_{E3}$	-	Relative contact area factor (slideways)
$a_L$	-	Life correction constant
$a_M$	-	Mating surface material factor
$a_T$	-	Temperature application factor
$B$	$\text{mm}$	Nominal bush width
$C$	$1/\text{min}$	Dynamic load frequency
$C_D$	$\text{mm}$	Installed diametral clearance
$C_i$	$\text{mm}$	ID chamfer length
$C_o$	$\text{mm}$	OD chamfer length
$C_T$	-	Total number of dynamic load cycles
$D_C$	$\text{mm}$	Diameter of burnishing tool
$D_{fl}$	$\text{mm}$	Nominal bush flange OD
$D_H$	$\text{mm}$	Housing Diameter
$D_i$	$\text{mm}$	Nominal bush and thrust washer ID
$D_{i,a}$	$\text{mm}$	Bush ID when assembled in housing
$D_J$	$\text{mm}$	Shaft diameter
$D_{Nth}$	$\text{nvt}$	Max. thermal neutron dose
$D_o$	$\text{mm}$	Nominal bush and thrust washer OD
$D_\gamma$	$\text{Gy}$	Max. Gamma radiation dose
$d_{ch,1}$	$\text{mm}$	Checking block diameter
$d_D$	$\text{mm}$	Dowel hole diameter
$d_L$	$\text{mm}$	Oil hole diameter
$d_P$	$\text{mm}$	Pitch circle diameter for dowel hole
$F$	$\text{N}$	Bearing load
$F_{ch}$	$\text{N}$	Test force
$F_i$	$\text{N}$	Insertion force
$f$	-	friction

Formula Symbol	Unit	Designation
$H_a$	$\text{mm}$	Depth of Housing Recess (e.g. for thrust washers)
$H_d$	$\text{mm}$	Diameter of Housing Recess (for thrust washers)
$L$	$\text{mm}$	Strip length
$L_H$	$\text{h}$	Bearing service life
$L_S$	$\text{mm}$	Length of stroke (slideway)
$N$	$1/\text{min}$	Rotational speed
$N_{osz}$	$1/\text{min}$	Oscillating movement frequency
$\bar{p}$	$\text{N}/\text{mm}^2$	Specific load
$\bar{p}_{lim}$	$\text{N}/\text{mm}^2$	Specific load limit
$\bar{p}_{sta,max}$	$\text{N}/\text{mm}^2$	Maximum static load
$\bar{p}_{dyn,max}$	$\text{N}/\text{mm}^2$	Maximum dynamic load
$Q$	-	Permissible number of cycles
$R_a$	$\text{mm}$	Surface roughness (DIN 4768, ISO/DIN 4287/1)
$R_{OB}$	$\Omega$	Electrical resistance
$s_3$	$\text{mm}$	Bush wall thickness
$s_{fl}$	$\text{mm}$	Flange thickness
$s_S$	$\text{mm}$	Strip thickness
$s_T$	$\text{mm}$	Thrust washer thickness
$T$	$^\circ\text{C}$	Temperature
$T_{amb}$	$^\circ\text{C}$	Ambient temperature
$T_{max}$	$^\circ\text{C}$	Maximum temperature
$T_{min}$	$^\circ\text{C}$	Minimum temperature
$U$	$\text{m}/\text{s}$	Sliding speed
$W$	$\text{mm}$	Strip width
$W_{U min}$	$\text{mm}$	Minimum usable strip width
$Z_T$	-	Total number of cycles
$\alpha_1$	$1/10^6\text{K}$	Coefficient of linear thermal expansion parallel to surface
$\alpha_2$	$1/10^6\text{K}$	Coefficient of linear thermal expansion normal to surface
$\sigma_c$	$\text{N}/\text{mm}^2$	Compressive Yield strength
$\lambda$	$\text{W}/\text{mK}$	Thermal conductivity
$\phi$	$^\circ$	Angular displacement
$\eta$	$\text{Ns}/\text{mm}^2$	Dynamic Viscosity



## Product Information

GGB gives an assurance that the products described in this document have no manufacturing errors or material deficiencies.

The details set out in this document are registered to assist in assessing the material's suitability for the intended use. They have been developed from our own investigations as well as from generally accessible publications. They do not represent any assurance for the properties themselves.

Unless expressly declared in writing, GGB gives no warranty that the products described are suited to any particular purpose or specific operating circumstances. GGB accepts no liability for any losses, damages or costs however they may arise through direct or indirect use of these products.

GGB's sales and delivery terms and conditions, included as an integral part of quotations, stock and price lists, apply absolutely to all business conducted by GGB. Copies can be made available on request.

Products are subject to continual development. GGB retains the right to make specification amendments or improvements to the technical data without prior announcement.

Edition 2016 (This edition replaces earlier editions which hereby lose their validity).

## Declaration on lead contents of GGB products/compliance with EU law

Since July 1, 2006 it has been prohibited under Directive 2002/95/EC (restriction of the use of certain hazardous substances in electrical and electronic equipment; ROHS Directive) to put products on the market that contain lead, mercury, cadmium, hexavalent chromium, polybrominated biphenyls (PBB) or polybrominated diphenyl ethers (PBDE).

Certain applications listed in the annex to the ROHS Directive are exempted. A maximum concentration value of 0.01% by weight and per homogeneous material, for cadmium and of 0.1% by weight and per homogeneous material, for lead, mercury, hexavalent chromium, PBB and PBDE shall be tolerated.

According to Directive 2000/53/EC on end-of life vehicles, since July 1, 2003 it has been prohibited to put on the market materials and components that contain lead, mercury, cadmium or hexavalent chromium. Due to an exceptional provision, lead-containing bearing shells and bushes could still be put on the market up until July 1, 2008. This general exception expired on July 1, 2008. A maximum concentration value of up to 0.1% by weight and per homogeneous material, for lead, hexavalent chromium and mercury shall be tolerated.

**All products of GGB, with the exception of DU, DU-B, SY and SP satisfy these requirements of Directives 2002/95/EC (ROHS Directive) and 2000/53/EC (End-of-life Vehicle Directive).**

**All products manufactured by GGB are also compliant with REACH Regulation (EC) No. 1 907/2006 of December 18, 2006.**

## Health Hazard - Warning

There are two separate aspects of health hazard which could arise from certain usage of DU materials.

### Fabrication

At temperatures up to 250 °C the polytetrafluoroethylene (PTFE) present in the lining material is completely inert so that even on the rare occasions in which DU bushes are drilled, or sized, after assembly there is no danger in boring or burnishing.

At higher temperatures however, small quantities of toxic fumes can be produced and the direct inhalation of these can cause an influenza type of illness which may not appear for some hours but which subsides without after-effects in 24-48 hours.

Such fumes can arise from PTFE particles picked up on the end of a cigarette. Therefore smoking should be prohibited where DU is being machined.

DU® and DU-B are trademarks of GGB.

Visit us on the internet:  
[www.ggbearings.com](http://www.ggbearings.com)



an EnPro Industries company

The Global Leader in High Performance Bearing Solutions

## **GGB Heilbronn GmbH**

Postfach 18 62 • D-74008 Heilbronn  
Ochsenbrunnenstraße 9 • D-74078 Heilbronn  
Industriegebiet Böllinger Höfe  
Tel. +49 7131 269 0 • Fax +49 7131 269 500  
eMail: [germany@ggbearings.com](mailto:germany@ggbearings.com) • [www.ggbearings.de](http://www.ggbearings.de)



HB103ENG11-15HN